




Division of Research
& Innovation

Snaplock Fiber Reinforced Composites Technology Applied to Overhead Sign Structures

Design, Construct, and Test a Fiber Reinforced Composite Overhead Sign Truss

Final Report

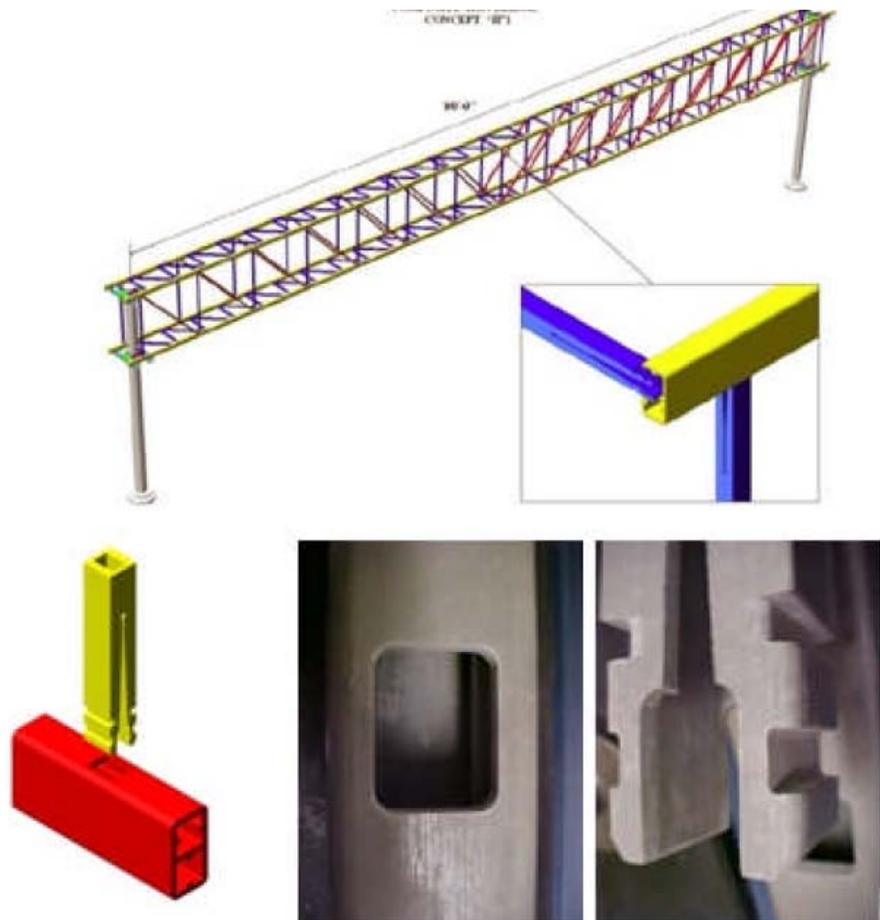

Snaplock Fiber Reinforced Composites Technology Applied to Overhead Sign Structures

Design, Construct, and Test a Fiber Reinforced Composite Overhead Sign Truss

Final Report

Report No. CA07-0246

December 2008

Prepared By:

Composite Support & Solutions Inc.
767 Channel Street
San Pedro, CA 90731

Prepared For:

California Department of Transportation
Engineering Services Center
1801 30th Street
Sacramento, CA 95816

California Department of Transportation
Division of Research and Innovation, MS-83
1227 O Street
Sacramento, CA 95814

DISCLAIMER STATEMENT

This document is disseminated in the interest of information exchange. The contents of this report reflect the views of the authors who are responsible for the facts and accuracy of the data presented herein. The contents do not necessarily reflect the official views or policies of the State of California or the Federal Highway Administration. This publication does not constitute a standard, specification or regulation. This report does not constitute an endorsement by the Department of any product described herein.

STATE OF CALIFORNIA DEPARTMENT OF TRANSPORTATION
TECHNICAL REPORT DOCUMENTATION PAGE
 TR0003 (REV. 10/98)

1. REPORT NUMBER CA07-0246		2. GOVERNMENT ASSOCIATION NUMBER		3. RECIPIENT'S CATALOG NUMBER	
4. TITLE AND SUBTITLE Snaplock Fiber Reinforced Composites Technology Applied to Overhead Signs: Design, Construct, and Test a Fiber Reinforced Composite Overhead Sign Truss				5. REPORT DATE December, 2008	
7. AUTHOR(S) Clem Hiel				6. PERFORMING ORGANIZATION CODE	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Composite Support & Solutions Inc 727 Channel Street San Pedro, CA 90731				8. PERFORMING ORGANIZATION REPORT NO.	
12. SPONSORING AGENCY AND ADDRESS California Department of Transportation Engineering Services Center 1801 30th Street Sacramento, CA 95816 California Department of Transportation Division of Research and Innovation, MS-83 1227 O Street Sacramento, CA 95814				10. WORK UNIT NUMBER	
				11. CONTRACT OR GRANT NUMBER DRI Research Task No. 0246 Contract No. 59A0343	
15. SUPPLEMENTAL NOTES .				13. TYPE OF REPORT AND PERIOD COVERED Final Report	
				14. SPONSORING AGENCY CODE 913	
16. ABSTRACT <p>This report paper summarizes progress on a research program to investigate the use of composite materials for overhead sign bridges, as well as the assembly of these structures without fasteners.</p> <p>A composite overhead sign bridge was designed and analyzed. The traditional profile shapes, which are in use for steel sign bridges, were not copied in composite materials. Instead two types "lineals" with a special rectangular cross sections for functionality were designed. The cross-sectional shape and fiber architecture of these tubes is dominated by the requirement for a "snap-fit" assembly. The complexities in geometry and fiber architecture can easily be handled by an automated "Pultrusion" process.</p> <p>Since Pultrusion-dies are expensive the "lineals" were first manufactured by hand lay-up, and resin infusion on wood tooling. The snap-fit joint created by both parts was subsequently assembled and tested in order to provide a proof of concept without expensive Pultrusion-dies or the added cost of die modifications.</p> <p>As a next step the most extensively loaded joint area in the sign bridge structure was assembled from the two Pultruded tubular sections and subject to the loads which were derived from the analysis. As such the load factors and failure modes have been established.</p> <p>This report outlines a research program undertaken at CSSI to investigate the feasibility of a sign structure which can be erected quickly. The feasibility of a fastenerless 90-ft sign truss in composite materials has been investigated.</p> <p>A two post sign truss with a clear span of 90 feet was selected as a benchmark. The layout of a fastenerless composite sign truss with two posts revealed significant weight savings. A newly developed composite "snap joint" which is pultrudable is the heart of this lightweight sign structure. Performance tests revealed that this joint has a static load capacity of more than 22,000 lbs.</p>					
17. KEY WORDS Composite materials, overhead sign truss, snap-fit assembly, feasibility, design, construction, analysis, testing			18. DISTRIBUTION STATEMENT No restrictions. This document is available to the public through the National Technical Information Service, Springfield, VA 22161		
19. SECURITY CLASSIFICATION (of this report) Unclassified		20. NUMBER OF PAGES 95 Pages		21. PRICE	

FINAL REPORT

DESIGN, CONSTRUCT, AND TEST A FIBER REINFORCED COMPOSITE OVERHEAD SIGN TRUSS

CONTRACT 59A0343

**Dr. Clem Hiel
Composite Support & Solutions Inc, San Pedro, CA.
767 Channel Street
San Pedro, CA 90731**

ABSTRACT: This report paper summarizes progress on a research program to investigate the use of composite materials for overhead sign bridges, as well as the assembly of these structures without fasteners.

A composite overhead sign bridge was designed and analyzed. The traditional profile shapes, which are in use for steel sign bridges, were not copied in composite materials. Instead two types “lineals” with a special rectangular cross sections for functionality were designed. The cross-sectional shape and fiber architecture of these tubes is dominated by the requirement for a “snap-fit” assembly. The complexities in geometry and fiber architecture can easily be handled by an automated “Pultrusion” process.

Since Pultrusion-dies are expensive the “lineals” were first manufactured by hand lay-up, and resin infusion on wood tooling. The snap-fit joint created by both parts was subsequently assembled and tested in order to provide a proof of concept without expensive Pultrusion-dies or the added cost of die modifications.

As a next step the most extensively loaded joint area in the sign bridge structure was assembled from the two Pultruded tubular sections and subject to the loads which were derived from the analysis. As such the load factors and failure modes have been established.

This report outlines a research program undertaken at CSSI to investigate the feasibility of a sign structure which can be erected quickly. The feasibility of a fastenerless 90 sign truss in composite materials has been investigated.

A two post sign truss with a clear span of 90 feet was selected as a benchmark. The layout of a fastenerless composite sign truss with two posts revealed significant weight savings. A newly developed composite “snap joint” which is pultrudable is the heart of this lightweight sign structure. Performance tests revealed that this joint has a static load capacity of more than 22,000 lbs.

The report consists of eight sections.

The introduction summarizes our findings about the use of composite materials in overhead sign structures throughout the world.

Section 2 provides the basic information on a benchmark overhead sign truss and discusses four concepts which were considered for a composite overhead sign bridge

Section 3 summarizes the material system identification

Section 4 provides details of the pultrusion manufacturing process including the fiber dispensing system, and the fiber impregnation system and sequence.

Section 4 provides information about quality control, including a trial assembly of a 30 ft section of the overhead sign bridge design.

Section 5 gives the analytical and test results. Part of this section is dedicated to a critical review of the snap joint design, its failure modes, and possible ways to improve the design. Also provided is a full structural analysis of a benchmark composite overhead sign truss for the load cases which are identified by AASHTO

Section 7 gives the summary and the conclusions for this project.

REPORT OUTLINE:

1. Introduction
2. Design Methods
3. Material System Identification
4. Manufacturing Process
5. Quality Control Procedures
6. Analytical and Test Results
7. Conclusions and Recommendations
8. References

1. INTRODUCTION

The application of composite materials has been pursued technically and commercially in a variety of structural engineering applications. These applications cover a very wide range from power delivery infrastructure and bridge decks to maritime docking structures. One documented case [1] explores the possibility of temporary composite structures within the British Rail network. It concerns temporary structures which assist in revenue earning after disruptions by supporting overhead electrification conductors and associated equipment and temporary footbridges to provide across track access without disruption of service.

On 28 November 1995, a CMS structure located on Interstate I-15 in San Bernardino County, California, failed. As a result more than 200 CMS structures throughout the state of California were inspected to determine the extent of wind-induced cracking in their welded components. Cracked welds were found in the post-to-base plate connections and in the arm-to-post welded connections.

Many of the Nation's DOT's have documented cases [2, 3] of sign-truss structures and signal mast arms made of steel and aluminum which have experienced fatigue-failures in the welds. In a number of cases composite materials have been used for the repairs [4]. Other recommendations for increased reliability range from insuring weld quality to dampers on the mast arms.

Repair of damaged aluminum truss joints of highway overhead sign structures using FRP.

By Fam, Amir; Rizkalla, Sami; Witt, Sarah

Publication: Construction and Building Materials

Date: Friday, December 1 2006

Abstract

An innovative repair technique is introduced for aluminum truss-type highway overhead sign structures, using fibre-reinforced polymer (FRP) sheets. The welded k-joints are typically subjected to excessive fatigue-induced cracking under the effects of wind and moving traffic. The repair technique proposed in this paper utilizes longitudinal FRP layers bonded to the diagonals and wrapped around the main chord to form alternating v-patterns, followed by additional circumferential layers for anchorage. Eight tests were conducted on four full-scale specimens. Weld

Figure 1 Use of Composite Materials to Repair Overhead Sign Structures

Figure 2 illustrates some of the weld fatigue problems experienced by NYDOT for aluminum sign bridges.





Figure 2 Weld Fatigue Failure in Aluminum Sign Bridge as Experienced by NYDOT.

These sign bridges have been repaired with FRP wraps, which functioned as crack arrestors, when bonded over the failed area.

The U.K. Highways Agency has been a leader in efforts to use composite materials for sign structures as illustrated in Figure 3.

U.K. FIRM DEBUTS COMPOSITE OVERHEAD SIGN STRUCTURES

The Specialist Structures Group of White Young Green (WYG, Headingley, Leeds, U.K., formerly CETEC Projects Ltd.) and the U.K. Highways Agency are developing a composite solution for motorway overhead sign structures. Ranging from 15m to 50m (49.2 ft to 164 ft) in length, the structures will span the entire roadway width in both traffic directions without a central support. Developed as an alternative to steel or concrete structures, many of which are reaching their design life limits, the composite structures offer lighter weight, easier transport and erection, greater durability and lower lifecycle costs.

WYG's project manager, Dr. Mark Leaity, notes that horizontal beams are infused, using vinyl ester resin, uni and biaxial glass reinforcements and balsa core. Supports are resin transfer molded. "There are no impending installations but there is a lot of interest in the U.K.," says Leaity. "The main barrier is cost." The company is exploring automated methods to make the product more cost-competitive.



Figure 3 Overhead Sign Structures in the U.K.

As mentioned in the article, sign structures are technologically possible, but the main barrier is cost. The U.K. effort evidently uses sandwich panel construction in conjunction with resin transfer molding (RTM). As such the overhead sign structure manifests itself as a composite boxbeam, which is not the most economic and lightest construction, especially not for the longer overhead sign structures.

Figure 4 illustrates another example of an overhead sign structure, also from the U.K, of a prototype structure on Motorway M25.



Figure 4 Composite Variable Message Sign Structure with Steel Post on the M25 Motorway in UK

This cantilever type is used as a variable message sign and is attached to a steel post. It's actual detail construction is unknown, but it is reasonable to assume that it is also an RTM type sandwich construction.

To the best of our knowledge, the examples shown in Figures 3 and 4 represent the state of the art in overhead sign structures.

In this report we have opted for an entirely different approach, which is to rely on automated pultrusion technology to manufacture truss elements which can easily be assembled into sign structures. This approach not only creates a light structure, but also makes it cost competitive with metal structures technology.

Additionally, composite materials are a natural for sign truss applications because of their inherent favorable fatigue characteristics, high damping, the fact that they don't corrode and thus for their inherent low maintenance potential. Composite sign structures have a substantially lower weight and can thus be installed with lighter equipment. Additionally the recent increases in the cost of energy, making steel, concrete, and transportation costs favor alternative solutions in the form of lightweight composite structures.

The research currently pursued by CSSI adds a novel element, which is the use of high performance structural snap joints. The state of the art has been discussed in a 1997 conference paper by Goldsworthy and Hiel [5]. These joints do not only provide for rapid

on-site assembly, but they also have shown the promise of substantial contributions to the structural damping capacity of the structure.

In an era where a twenty minute tie-up wastes over 2000 vehicle hours, causes a 3 mile backup and takes 2.5 hours to clear the world is moving towards IVHS (Intelligent Vehicle Highway System) [6] for which the “stealth” like qualities of fastenerless composites truss structures are an asset.

The section below illustrates the various design concepts which were developed during this project.

Various approaches have been used towards the conceptual design of the overhead sign structure as discussed below:

1.1 Concept #1 Pultruded beam and corner elements

The Overhead Sign-Truss is conceptualized as truss members, shown in Figure 6, which can easily be assembled together with an interlocking type mechanism without the use of mechanical fasteners or adhesives.

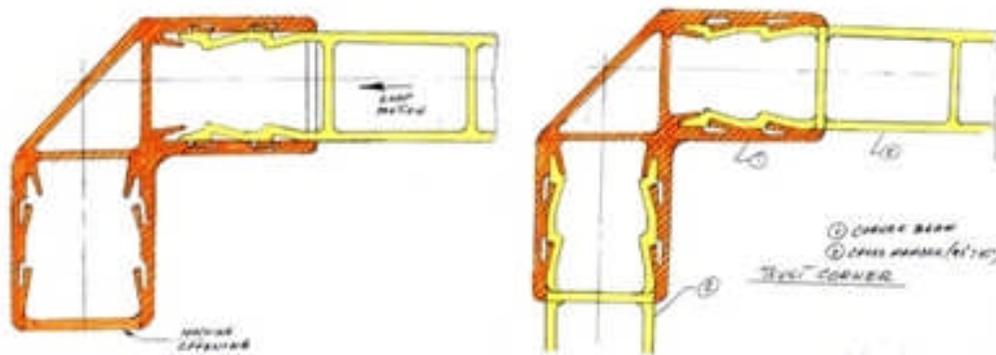


Figure 6 Concept for Sign Structure new Corner Joint

Figure 7 shows a pultruded connection detail that has sufficient flexibility to snap-fit into the pultruded corner elements.

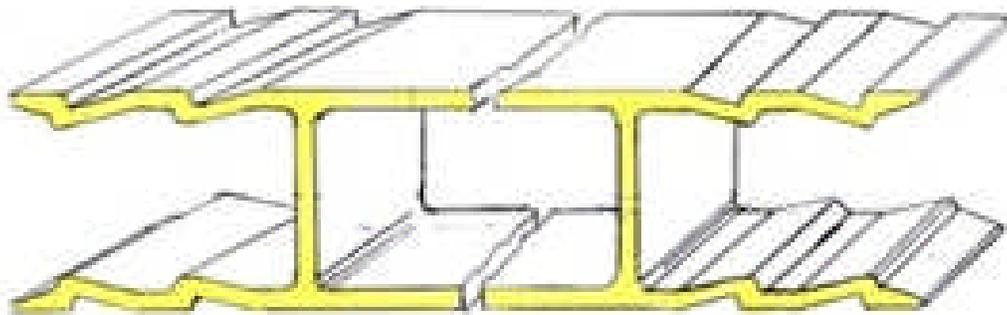


Figure 7 Pultruded Connection Detail

Figure 8 shows a slight deviation of this concept with more complicated corner joints.

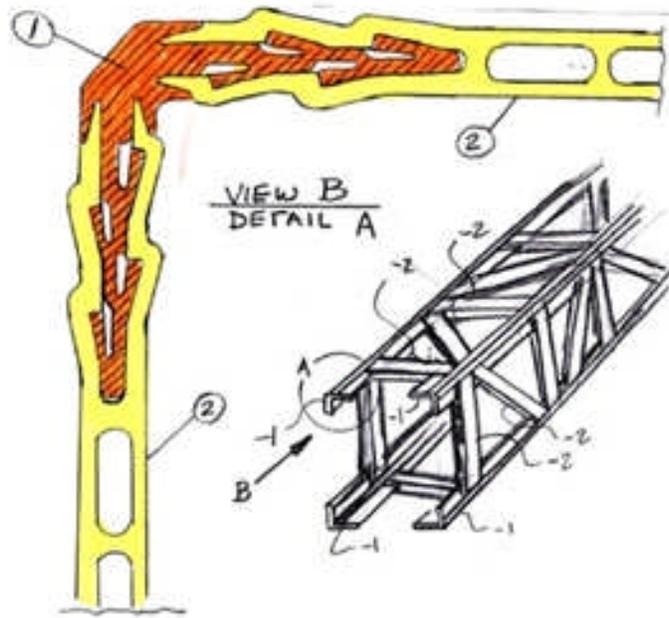


Figure 8 Other Concept for Sign Bridge Corner Joint

The second concept emphasizes the pultrusion of 6 to 8 ft wide sandwich panels or ribbed hollow panels. These panels are then cut along certain angles to provide the truss members which are needed for the fastenerless assembly of an overhead sign structure.


1.2 Concept # 2

Figure 9 is entirely novel and virtually eliminates the machining which was an integral part of the first generation snaplock joints which were discussed in the background section above.



Figure 9 Pultruded Panel

The angled cross-members utilized for assembly and shown in detail in Figure 10 can be obtained by cutting a wider panel at the appropriate angle. This approach as visualized in

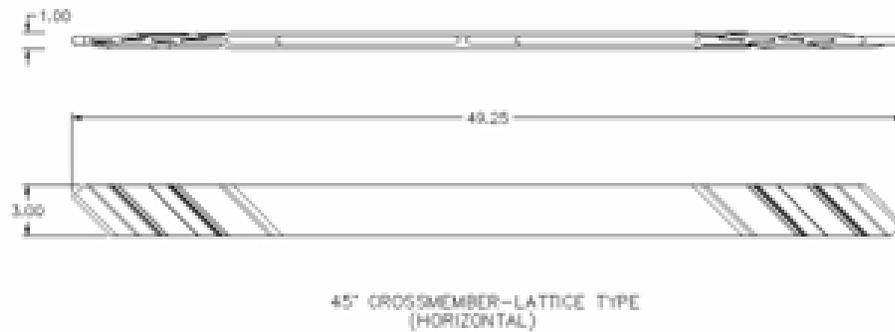

TITLE: FASTENERLESS JOINT
 CATEGORY: HEAVY STRUCTURAL MEMBERS FOR INFRASTRUCTURE
 JOINT TYPE: UPPER/LOWER BEAM WITH VERTICAL/DIAGONAL MEMBERS

Figure 10 Angled cross-members and novel idea for pultrusion without the need for NC-machining

A key element of this task is the design of the fiber architecture which needs to be defined early on. A folded fiber architecture not only allows the joint to be functional but also introduces adequate interlaminar tension and shear resistance which translates into good durability. This is an example of our approach to designing durability into a structure by making vital load paths fiber dominated.

Another concept that was pursued was that of an “Isotruss” structure.

1.3 Concept # 3

Figure 11 shows an “Isotruss” structure which was assembled by snap-joining of tubular elements.

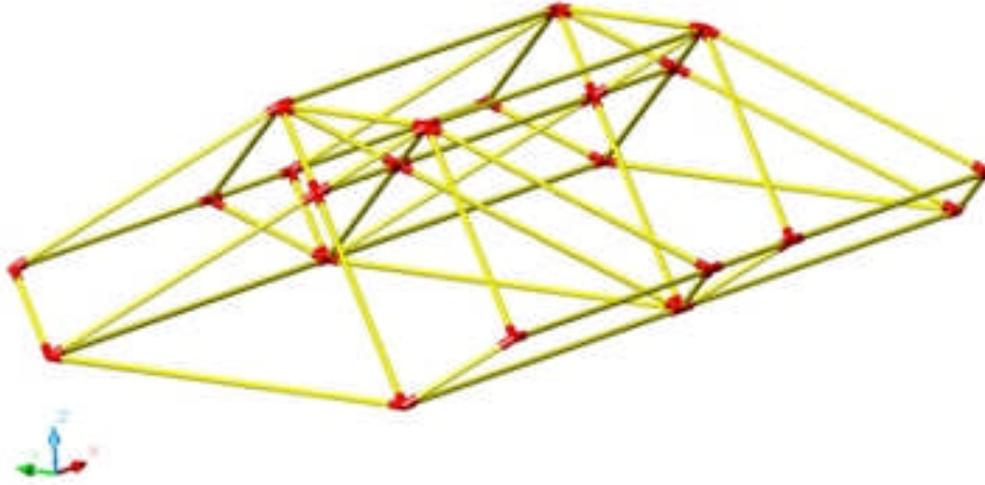


Figure 11 Isotruss Structure

This type of structure derives its stiffness from its geometry, much in the same sense as the geodesic structures which were designed by Buckminster Fuller.

Figure 12 shows concepts of the various joint configurations which would allow for snap fit assembly of these tubular structures.

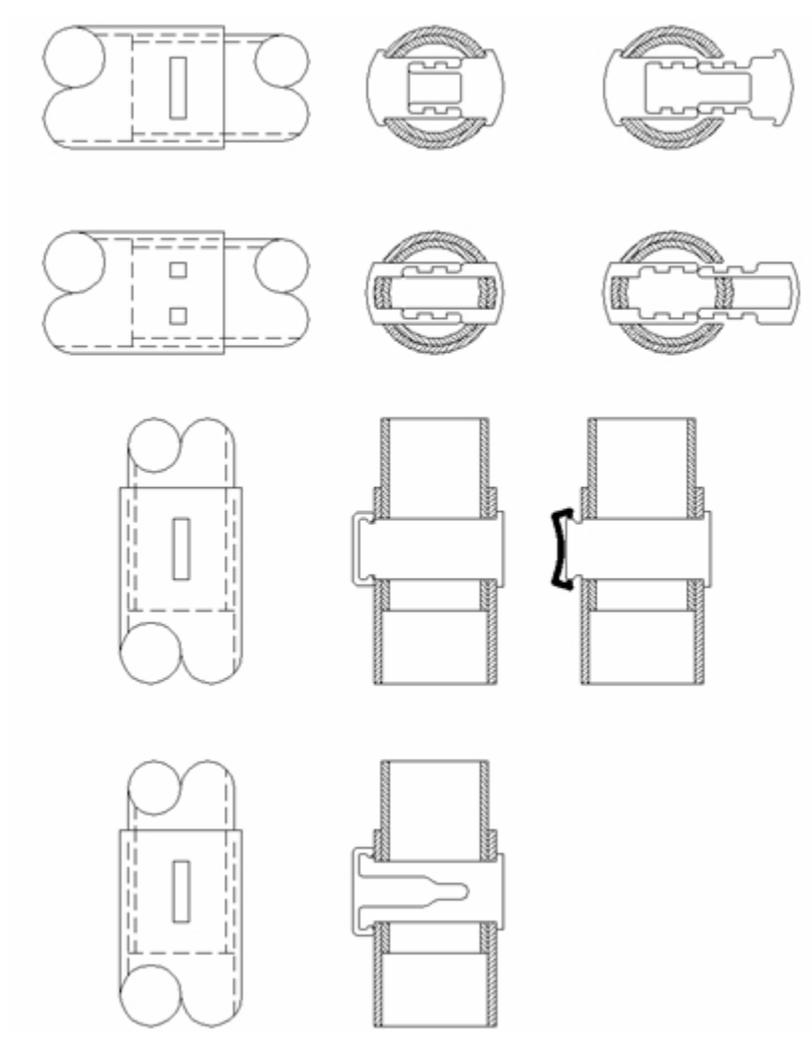


Figure 12 Joint Configurations for Assembly of Tubular Structures

Figures 13, and 14 shows the actual assembly sequence of a complicated truss joint.



Figure 13 Joint Halves

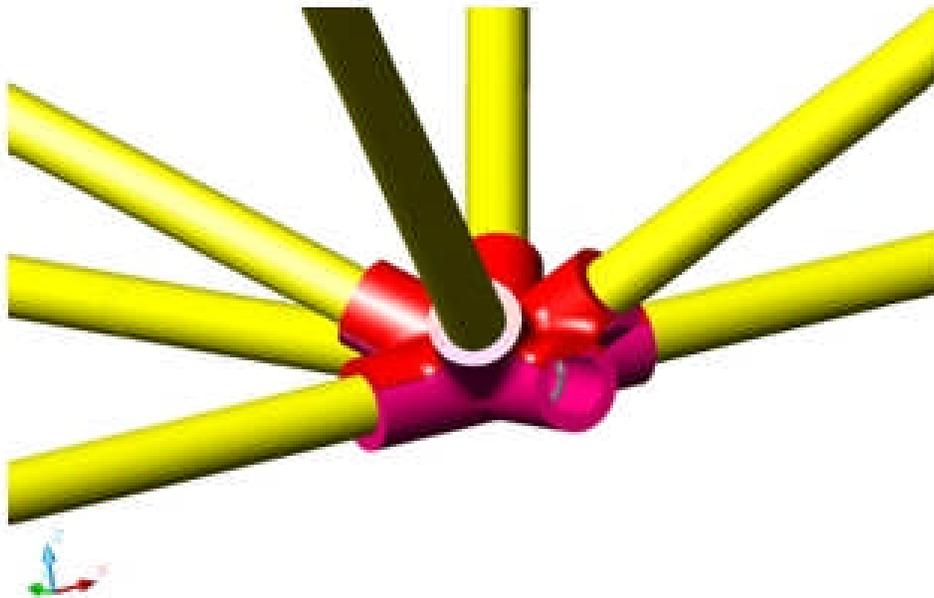


Figure 14 Joint halves Assembled

The concept that is discussed below is a more traditional snap-joint with a pultrusion that can accept cross-members in orthogonal directions.

Concept # 4

Figure 15 illustrates detail of two perpendicular cross members entering the longitudinal beam.

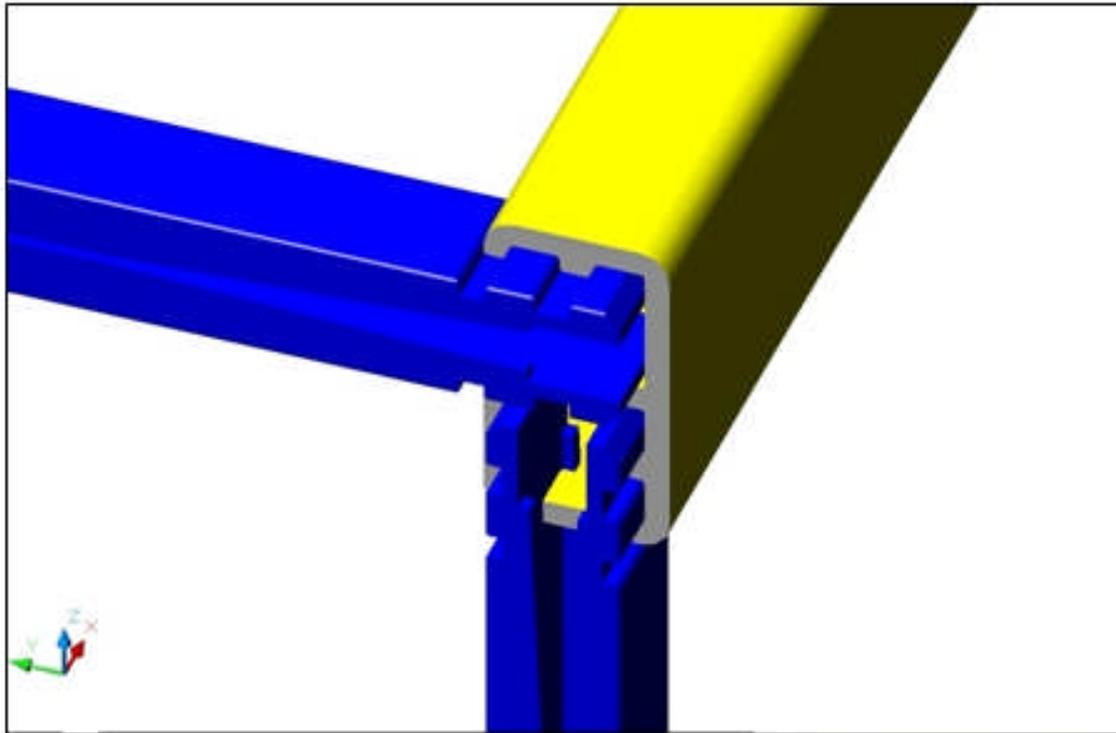


Figure 15 Orthogonal Cross Member Entrance

Because this concept showed a lot of promise, we decided to prove its manufacturability by resin infusion. Figure 16(a, b) shows the snap joint which was made in this way. The reason for using resin infusion was that this is the cheapest way to create a hardware model of the concept. We did however respect at all times the fiber architecture in such a way that the part could later be manufactured by pultrusion.



Figure 16 a, b Snap-joint infusion and finished snap joint assembly

Figure 16a illustrates the infusion setup. The operator is using an ultrasonic leak detector to eliminate vacuum leaks at the edges of the vacuum bag and at the fittings.

Figure 16b shows the finished snap-joint. Because of the merit of this joint configuration, it was decided to select this concept for implementation.

The fastenerless (snap joint) composite configuration is reproduced in Figure 17.

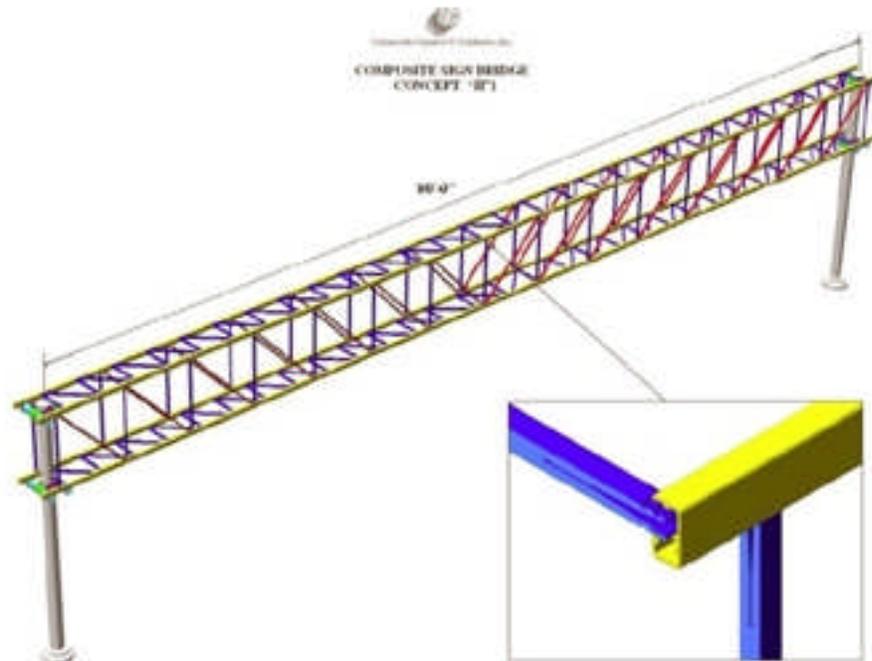


Figure 17 Benchmark Composite Sign Truss

The detail inset in Figure 17 shows the fastenerless joint (snap joint) configuration. The two cross-members (bleu) snap into what is essentially a boxbeam (yellow) with two entirely separated cavities.

The weight estimate of the composite sign truss is given in Table-II

WEIGHT OF COMPOSITE STRUCTURE (CONCEPT II)
(SIGN WEIGHT NOT INCLUDED)

LENGTH: 90 ft
HEIGHT: 76 in
WIDTH: 36 in

ITEM	DESCRIPTION	QTY	LENGTH (ft)	WEIGHT (plf)	TOTAL
1	Chord 5.125x2.75x.375	4	90	5.1	1836.0
2	Vertical 2x2x.25	32	6.33	1.95	395.0
3	Diagonal 2x2x.25	30	8.5	1.95	497.3
4	Wind Lateral 2x2x.25	58	2.9	1.95	328.0
5	Wind Diagonal 2x2x.25	56	4.2	1.95	458.6
TOTAL					3514.9 lbs

Table II Weight Estimate of Composite Sign Truss

The total weight comes out to 3515 lbs which is less than 1/3th of the weight of the benchmark steel sign truss.

3. MATERIAL SYSTEM IDENTIFICATION

The material system consists of E glass fiber and Vinylester resin.

The E-glass has the multipurpose sizing which is compatible with vinylester resin.

The vinylester resin has been formulated as shown in the table below.

RAW MATERIAL	LOT NO.	1 2 3 4 X-SMALL	1 2 3 4 SMALL	1 2 3 4 MEDIUM	1 2 3 4 LARGE	1 2 3 4 X-LARGE	PROCE DURE	MIX NO.
Dow 640-900		7.17 Lbs. (3240grams)	14.29 Lbs.	28.57 Lbs.	57 Lbs.	114 Lbs.	Charge to mixer. Start agitation.	1 2 3 4
PS125/PUL24/ Molgard X		0.11 Lbs. (50 grams)	0.22 lbs. (100 grams)	0.43 Lbs (200 grams)	0.88 Lbs. (400grams)	1.76 Lbs (800grams)	Add.	1 2 3 4
BYK 515		0.025 Lbs. (10 grams)	0.05 Lbs. (20 grams)	0.09 Lbs. (40 grams)	0.18 Lbs. (80 grams)	0.35 Lbs. (160 grams)	Add.	1 2 3 4
Rebus Beige pigment-45204		0.18 Lbs. (80 grams)	0.35 Lbs. (160 grams)	0.70 Lbs. (320 grams)	1.40 Lbs. (635 grams)	2.80 Lbs. (1270 grams)	Add.	1 2 3 4
ASP 600		1.43 Lbs. (650 grams)	2.85 Lbs. (1295 grams)	5.71 Lbs. (2590 grams)	11.40 Lbs. (5180grams)	22.8 Lbs	Add. Mix until uniform.	1 2 3 4
UV 5411		0.03 Lbs (10 grams)	0.05 Lbs. (23 grams)	0.10 Lbs. (45 grams)	0.20 Lbs. (90 grams)	0.40 Lbs. (180 grams)	Add.	1 2 3 4
Perkadox 16		0.04 Lbs. (20 grams)	0.09 Lbs (40 grams)	0.175 Lbs. (80 grams)	0.35 Lbs. (160 grams)	0.70 Lbs. (320 grams)	Premix with styrene.	1 2 3 4
ESPEROX 570P		0.04 Lbs. (16 grams)	0.07 Lbs. (33 grams)	0.14 lbs. (65 grams)	0.28 Lbs. (130 grams)	0.57 Lbs. (260 grams)	Add.	1 2 3 4
ESPEROX 10		0.015 Lbs. (8 grams)	0.03 Lbs. (15 grams)	0.07 Lbs. (30 grams)	0.13 Lbs. (60 grams)	0.26 Lbs. (120 grams)	Add.	1 2 3 4
							Mix well.	
BATCH SIZE		8.95 Lbs.	17.90 Lbs.	35.80 Lbs.	71.60 Lbs.	143.20 Lbs.		

TIME	RESIN TECH	RESIN TEMP.	BROOKFIELD VISCOSITY, LVF SPINDLE 3, 30RPM, @77°F: (1500-1700cps)	180F SPI GEL TIME, Min., CURE TIME, Min., LPE, °F: (0.5-1.5/1.5-2.5/340-370)	RESIN MIX TIME, MIN.
------	---------------	----------------	--	--	-------------------------------

Table III Resin Formulation

The fiber layup schedules are provided in the drawing package that is attached as an appendix.

The structural properties of the pultruded sections were determined as:

- EL = 3.5 Msi (ASTM C1557)
- GLT = 0.425 Msi (ASTM D4475)
- Poisson Ratio: 0.33 (ASTM C1577)

These values a higher than for traditional, non-structural pultrusions which typically have an E modulus of 2.6 Msi.

Fiber volume fractions have been determined on the basis of weight measurements, and they are well over 50% for all samples tested.

4. MANUFACTURING PROCESS

Pultrusion is a continuous fabrication method, and as such it has become a preferred manufacturing method for most of the composite structures which have been pursued commercially in structural engineering. Our company (CSSI) owns two industrial capacity pultrusion machines dedicated to pultrude the hardware for extended test configurations and for full size sign trusses.

The components of the sign truss have been designed so that they can be fabricated by the pultrusion process that is schematically shown in Figure 18.

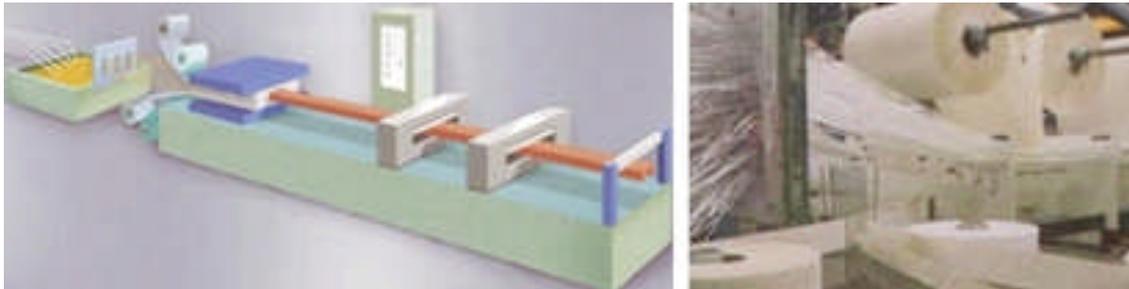


Figure 18 Fabrication of Sign Truss Elements by Pultrusion Process

Figure 19 shows a drawing of the fiber dispensing system.

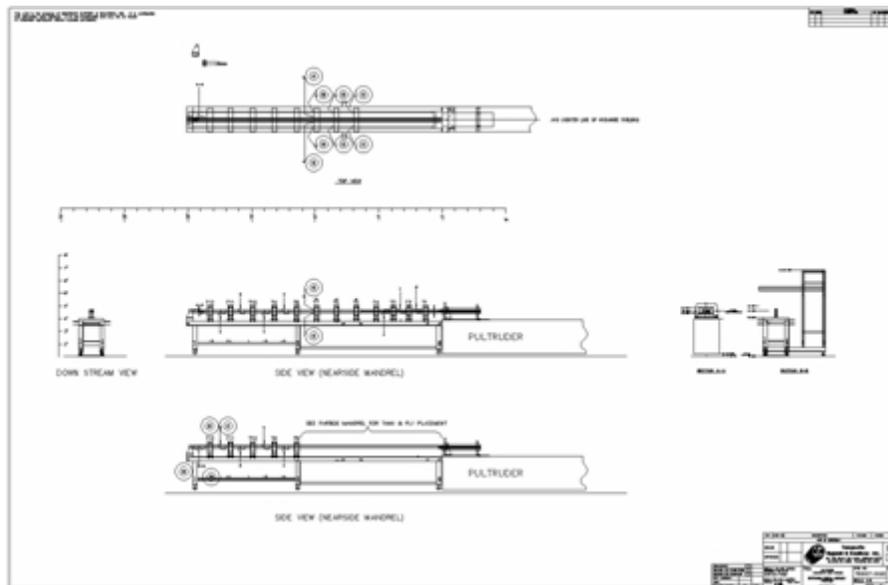


Figure 19 Fiber Dispensing System

This combination of fiber delivery towards the pultrusion-die and impregnation with resin in the process is the heart of the pultrusion operation.

Figure 20-22 show actual images of the pultrusion setup



Figure 20 Global view of the Pultrusion Setup



Figure 21 Detail of fiber Dispensing



Figure 22 Pultruded Component Exiting the Die

Figure 23 shows the pultruded elements which are stored for further machining and finishing operations



Figure 23 Finished Pultrusions

5. QUALITY CONTROL PROCEDURES

The quality control and storage of resins and fibers was conducted according to ASTM requirements.

The proper design of the fiber dispensing system is key to the quality of the pultruded components.

Figure 24 shows the section of a pultruded cross-member.

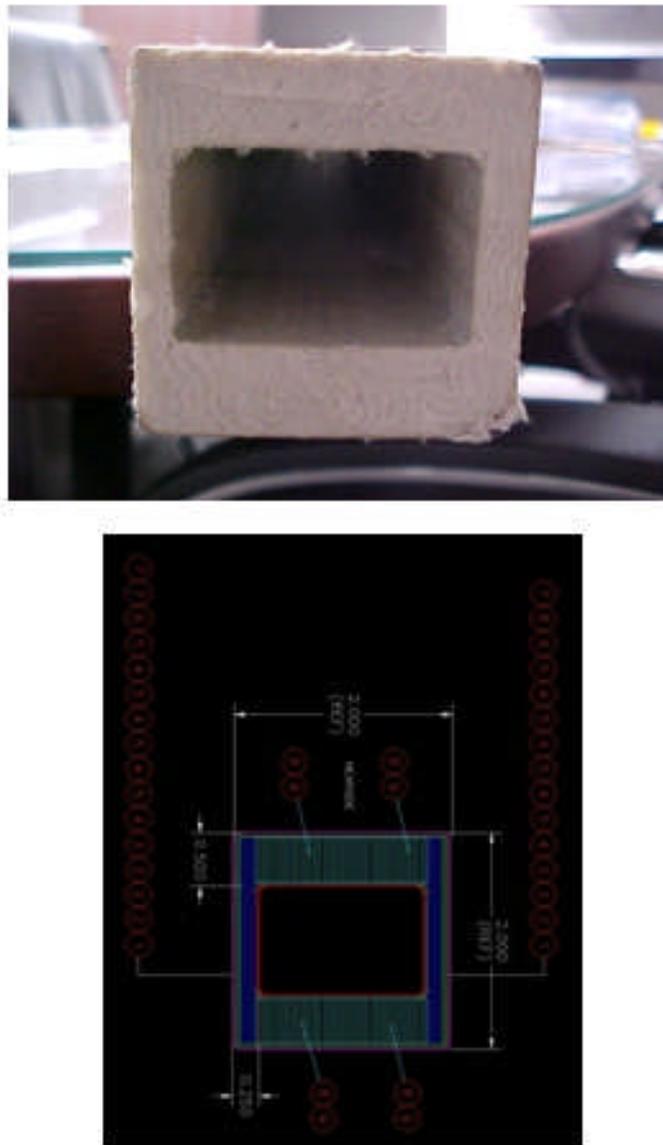


Figure 24 Section of Pultruded Cross-Member

These sections were examined for fiber density, and fiber distribution. Cuts were made every 60 ft and examined. No process variables were changed between cuts in order to assure the consistency of the pultruded component.

An important element in the determination of quality was in the ability to assemble the truss structure.



Figure 25 Assembled Overhead Sign Structure



Figure 26 Assembled Overhead Sign Structure



Figure 27 Detail Joint of Assembled Overhead Sign Structure

The connection of the truss to the vertical pole is shown in Figure 28

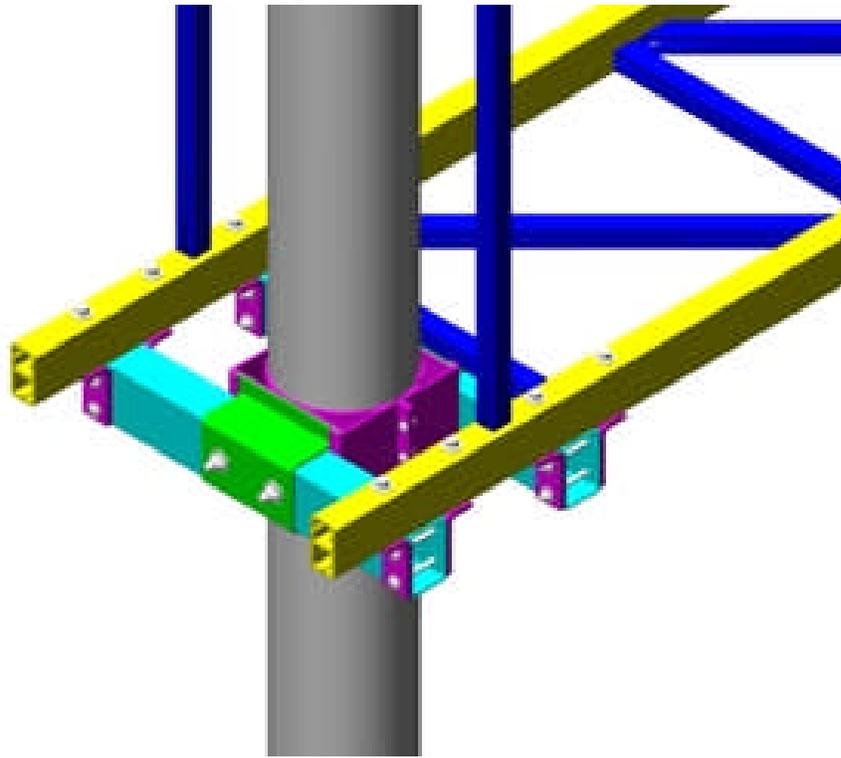


Figure 28 Connection of Truss to Vertical Pole

6. ANALYTICAL AND TEST RESULTS

Structural “snap-fits” for composite materials are a path-breaking approach for composite structures assembly which is capable of revitalizing some key opportunities for the U.S. industry and to define the tools, techniques, and ideas that can help put our efforts on a broad science and engineering footing.

Figure 29 illustrates our concept of creating a structural connection between two profiles without the need for fasteners.

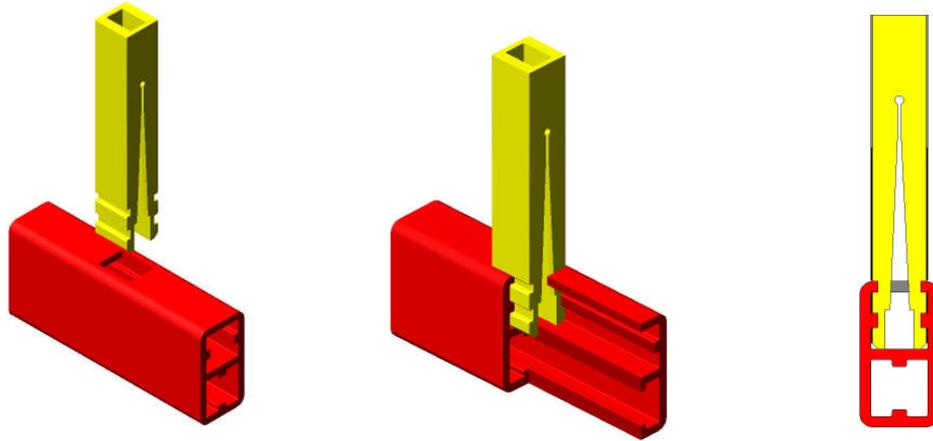


Figure 29 Snap Fit for Creating a Structural Connection

The yellow and the red profile are preferably fabricated by pultrusion, although we have used resin infusion for samples and small series as well. The methodology could be used with any of the composites manufacturing methods because snap-fit technology is merely a way of thinking about assembly and not tied to any particular method of manufacturing.

As a demonstration of the path-breaking potential of snap-fits we assembled the 9.14 meter (30 ft) truss structure shown in Figure 30 only 15 minutes.



Figure 30 Trial assembly of Snap-fit Truss Structure for this Project

The assembly sequence and steps have been documented in a separate internal report [9], which will be the basis for a future paper in a refereed Journal on composite materials technology.

The assembly in Figure 30 illustrates the ultimate goal for which we are developing this very cost competitive new assembly technology. The entire structure took only 15 minutes to assemble versus an estimated 2 hours for an equivalent metal structure. This result shows the practicality and the applicability of this approach and the opportunities which it embodies for further research and commercial application. By developing snap-fit technology for composite materials, we enable U.S. industry to remove the most formidable barrier that they are facing. This barrier is cost! Composite materials are always more expensive than traditional materials. Purchased cost or installed cost almost always favors the status quo. The U.S. industry is shoveling water upstream when it tries to overcome this barrier head-on or when they ask their customers to modify their perceptions and practices, or ask their customers to embrace “life-cycle” costing.


Figure 31 shows the snap fit connection which was shown above in Figure 30 as it is being loaded in a test frame. For reference we call this the benchmark snap-fit.



(a)



(b)

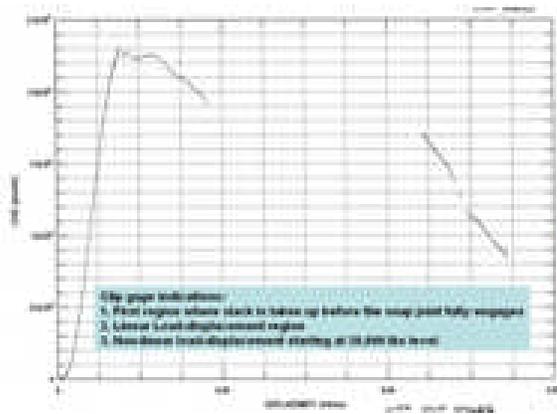

(c)



(d)

Figure 31 Benchmark Snap-Fit loaded in the Testing Machine

The load carrying capacity of the benchmark snap-fit is in the 104,540 N (23,000 lbs) range. We notice only a slight non-linearity prior to reaching the maximum load. This means that there are few non-linear phenomena acting. The snap-fit continues to carry a significant load once it has passed the maximum load point. This is shown further in results shown in Figure 37.

Figure 3d shows the setup of the snap-fit for compression loading. It was observed that the compression strength was on average 15% higher for all observed load cases.

SNAP-FIT FAILURE MODES

We did examine the failure mode of our benchmark snap-fit. Figure 32 shows the cracked component, after the joints was taken apart. It points to visible and stable cracking caused by a stress concentration at the radiussed corner of the opening in the double boxbeam part. This stress concentration could be alleviated in a number of ways



Figure 32 Critical Review of failure mode(s)

We notice that cracking has initiated at the corners and has then spread in the lengthwise direction of the part. This is explained by the stress concentration created by the small radius in the rectangular window opening. The corner had only a slight radius of 1/8". This radius gives us a stress concentration of a magnitude which was determined both theoretically and experimentally.

Residual stresses may be a factor, since the corner of the larger profile is participating in the load transfer as shown in Figure 33

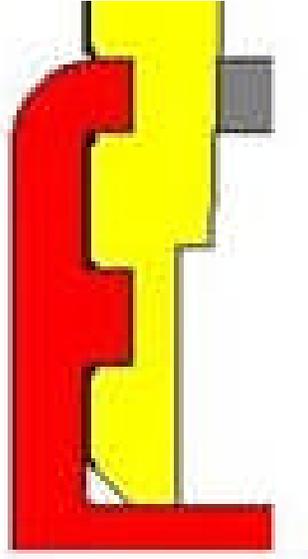


Figure 33 Contact surfaces

This could be determined by using a low shrink resin such as epoxy instead of the currently used vinylester.

Figure 34 shows the actual drawing of the fiber architecture. The table details the stitched fabric, the unidirectional fiber and the continuous strand mat. The resin was an Ashland Momentum vinylester resin. The orthotropic stiffness and the volume fraction were determined on the basis of this information.

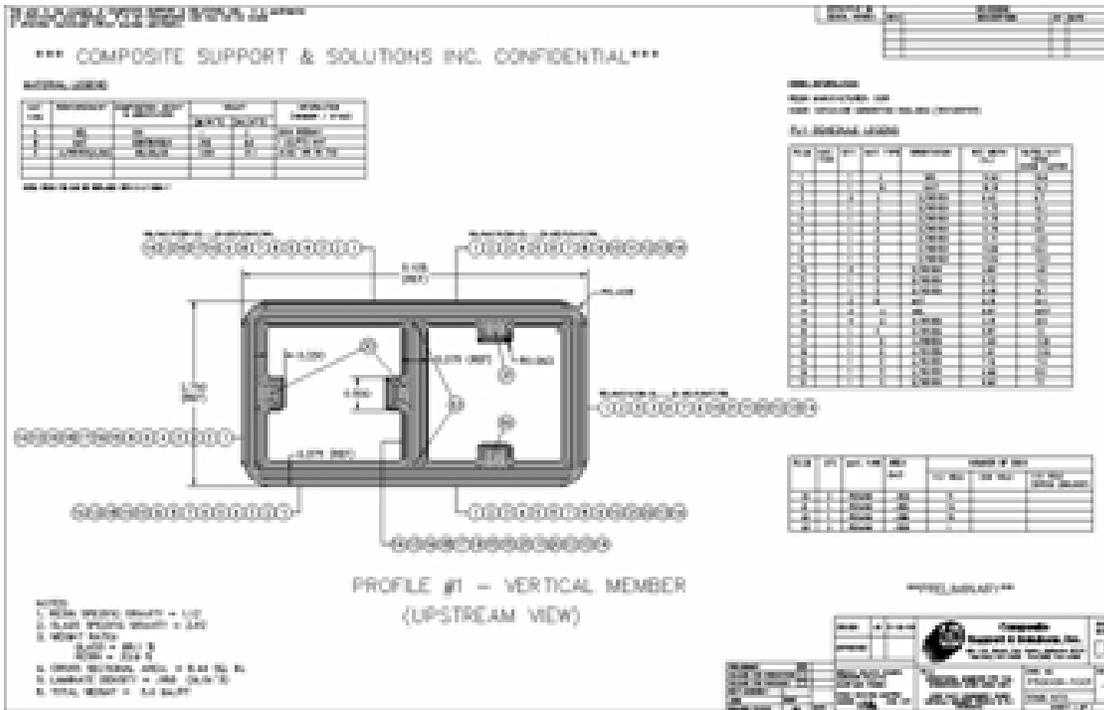


Figure 34 Fiber architecture

It was determined that this part has a 64% volume fraction of fibers by volume.

An examination of literature sources [10, 11] related to corner stress concentrations of plates with a square hole in bending has produced figures 35 a, b.

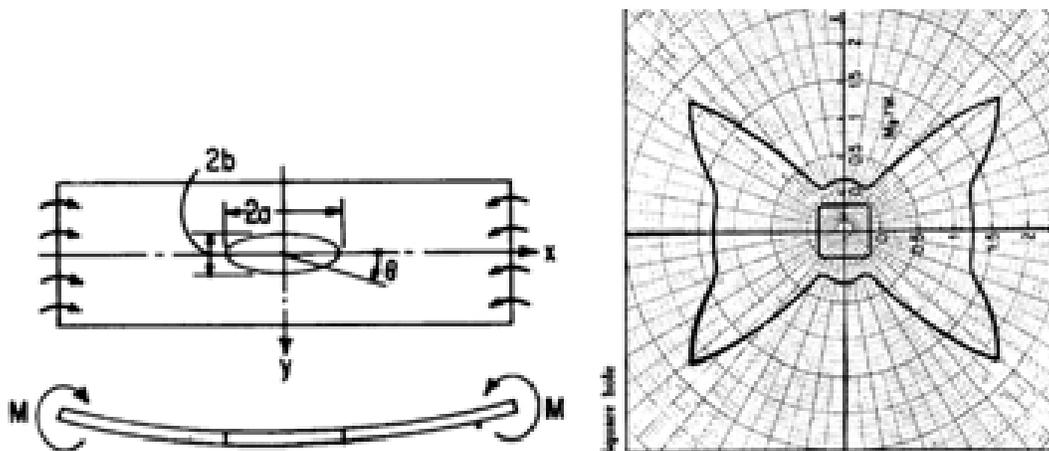


Figure 35 a, b Stress Concentration around a Square Hole in Bending

A stress concentration factor of 2.38 has been reported at the sharp corner.

A critical examination of the other component (the insert) revealed that there was no damage or cracking. This is due to the folded fiber architecture which we devised for this component. So far we have never been able to fail this component. It will be proposed to do this in our initial Phase-II effort, but this component does not appear to be a limiting factor.

STRESS/ STRAIN OBSERVATION METHOD TO OBSERVE THE SNAP-ENGAGEMENT AREA

Our company has direct working experience and operating knowledge with photoelastic coatings (photostress), moiré-Interferometry, and speckle-Interferometry. Based on the critical review of the failure modes in task 1, and based on communications with industry experts, we selected the photostress method [12, 13] for further examination of the areas of interest.

The Photostress method was invented by Dr. Felix Zandman [14]. It consists of bonding a transparent photoelastically sensitive plastic to the composite as shown in Figure 8. When putting the composite under stress, the stress equally affects the plastic. The plastic stretches in the same way as the composite it is bonded to. Its surface assumes the same deformations as the surface of the composite. The plastic has become a sensor for changes in the composite surface. Instead of speculating on equivalencies as is done in traditional transmission photoelasticity, this technique allows us to look at, and investigate the real thing.



Figure 36 Photostress method Applied to Composite Snap-Fit

The area of interest is the rectangular window with the rounded corners, which is the failure area as we discussed above.

The photoelastically sensitive plastic sheets were first calibrated in bending. The objective was to determine the fringe constant. The obtained value was 23 Mpa/ fringe. The detailed procedure has been outlined in a separate internal report [15].

Although the photoelastic method had fallen back with the emergence of FE (finite element) methods, it has made a come-back as is illustrated in ref's [16-18] which date from 2003 and 2006 and which investigate stress reduction and fatigue sensitivity in traditional bolts.

THREE DIMENSIONAL FINITE ELEMENT MODEL FOR BENCHMARK SNAP FIT SIMULATION AND IMPROVEMENT

Figure 37 shows the three dimensional model that was used for finite element implementation.

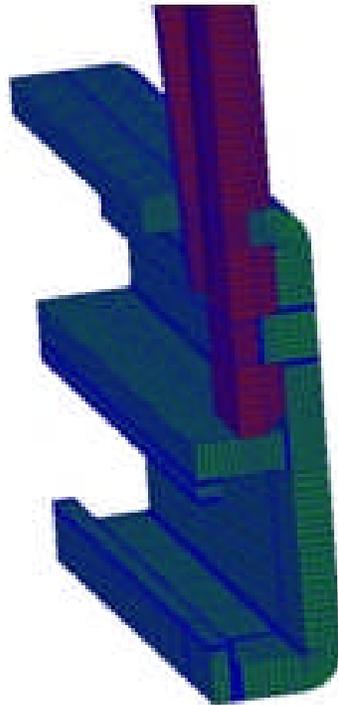


Figure 37 Three dimensional Snap-Fit FE-model

The CAD-file was transferred to Patran [19], which was used to mesh the geometry. The FE analysis was performed with NASTRAN. We performed a linear stress analysis, as shown in Figure 38, and assumed a uniformly distributed engagement load distribution applied by the insert.

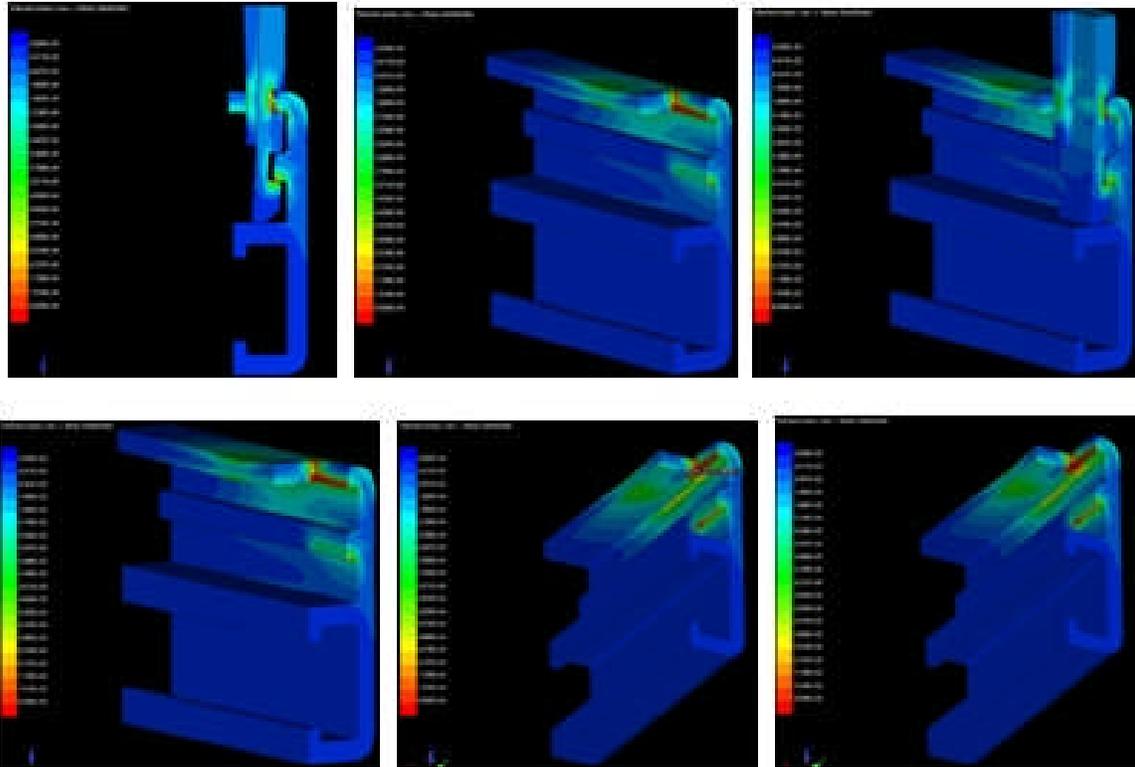


Figure 38 Typical Stress Distribution at the corners of the Window Section

The obtained stress distribution clearly puts most of the load into the engagement area around the window. The second, and lower, engagement protrusion is lighter loaded. An increase in the stiffness of the load path that engages this lower protrusion would help to equalize the load sharing between both engagement areas.

Additional FE analysis was performed on models with an increased radius at the window corner [20]. It was found that a 0.5" radius was most practical in that it would delay the onset of cracking and at the same time be feasible from a manufacturing standpoint. These results are, to the best of our knowledge, the first to be obtained on a structural snap-fit configuration. Our plan is to perform a refined analysis in Phase-II with contact elements, which will serve the more complicated loading cases which occur in the truss-type configurations such as was shown in Figure 2.

TEST PLAN FOR SNAP-FIT

The test plan was written as an internal report [21]. It outlines the tension and compression tests which needed to be performed on the snap-fit. It also outlines the observations which needed to be made with the photostress method. The test plan called for three different window radius configurations in addition to the baseline snap-fit configuration.

SNAP-FIT SAMPLES FOR WHOLE FIELD OBSERVATION AND PERFORM TENSILE AND COMPRESSION TESTS ACCORDING TO TEST PLAN

Figure 39 gives a global view as we gradually step back and observe the polariscope and the Instron testing machine which is used to load the snap-fit samples.

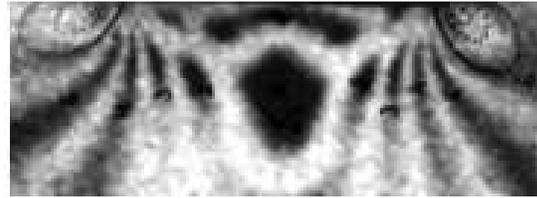


Figure 39 Photostress Method Applied to Snap-Fit

On the left we observe the computer control of the testing machine. The area of interest is thus located inside one of the cells of the double boxbeam. As such any strain or stress observation method which we select needs to be capable of observing stresses and or strains by a reflection method, and needs to work within the very confined area described. This task basically duplicates the setup in Figure 3, but with this difference that the observations are dedicated to determining the stress concentration for various radii of the window corners.

EXAMINE EXPERIMENTAL AND THEORETICAL RESULTS

Figure 40a shows a view through the reflection polariscope as the sample is prepared for loading. The development of photoelastic fringes was observed as shown in Figure 39b.



(a)

(b)

Figure 40 Photoelastic Fringe Pattern

This observation was made at a load level of 22,727 N (5000 lbs.) The fringes which we observe are the geometric locations of all points on the composite surface which have the same diameter of the Mohr circle. We labeled the fringes and observed they increase at the corner to an order of nine (9).

Figure 41 illustrates the first cracks which were observed at 83% of the ultimate failure load.



(a)

(b)

(c)

Figure 41 First cracks observed in the Snap-Fit

This observation sets the stage for the improved understanding of snap-fits. We now know that the limiting factor on the strength is the stress concentration at the window corners. In order to improve the snap-fit this stress concentration has to be reduced first. This can be achieved with the rounded window configuration which is shown in Figure 40c.

GUIDELINES FOR FUTURE GENERATIONS OF STRUCTURAL SNAP FITS

The guidelines for future generations of snap fits can be summarized as follows:

- The window radius is an important parameter for the strength of the snap-fit
- A window radius of 0.5" shows a potential for strength increase of 30%
- A “doubler” around the window section would further reduce the concentration around the window and thus further increase the strength of the snap-fit.
- The disadvantage of a doubler is that it requires an extra fabrication step and a secondary bonding step
- A design philosophy which creates a local stiff load path to minimize bending around the window would be beneficial
- For our current snap-fit design we used vinylester resin. Since this has a higher shrinkage than epoxy resin it is likely to set-up internal stresses which decrease the strength capacity of the baseline snap-fit. The use and the benefits of epoxy resin should be determined. The validity of this statement is supported by Figure 14 which compares the interlaminar strength of polyester and epoxy materials [14]. This data shows a potential for increasing the strength by a factor of 1.5 by selecting epoxy for the manufacturing process.

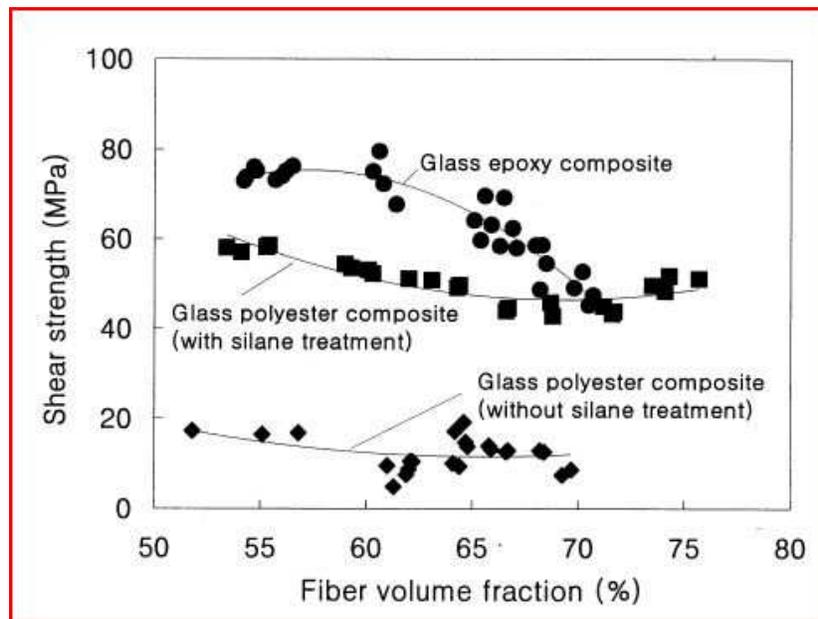


Figure 42 Improvement of Interlaminar Shear Strength [from Lee, 2001]

We should point out however that we expect the interlaminar shear strength for the vinylester-glassfiber composite which was used in this work to be higher than Lee's results for polyester. The glassfiber which we used had received the silane treatment. Figure 42 also indicates that our fiber volume fraction of 64% may be too high. When using epoxy a fiber volume fraction of 58% seems optimal.

INCREASE THE LOAD CAPACITY OF BASELINE SNAP FIT (SSF-2) TO THE 136,363 - 181,818 N (30,000-40,000 LBS) RANGE

It was determined from the analysis that a radius of 12.5 mm (0.5"), as shown in Figure 43, would have a beneficial effect on load capacity and at the same time be manufacturable.



Figure 43 Snap-fit Geometry change for increased load capacity

It is noted from Figure 42c that the cross-member insert also needed to be radiussed in order to fit into the window.

Figure 44 illustrates the improvement in the local stress distribution at the rounded window corner. As was the case for the benchmark snap-fit, this stress distribution was observed at a load level of 22,727 N (5000 lbs).

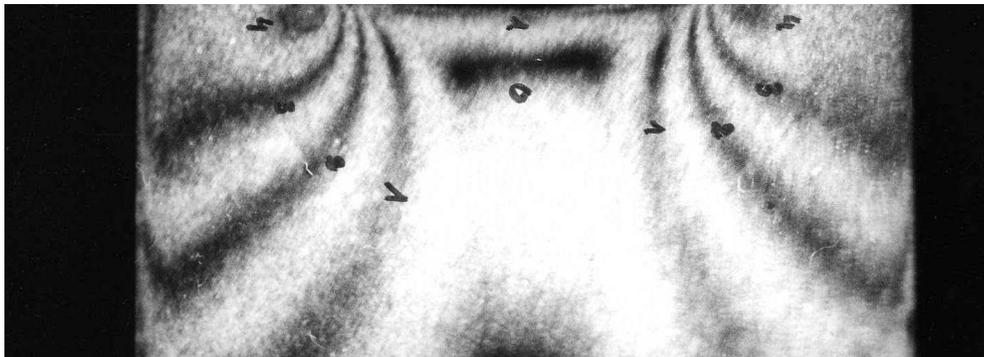


Figure 44 Photoelastic result with rounded window corner

As before, we labeled the fringes and observed that they are slightly higher than 4 at the corner. This means that the stress concentration is roughly half of what it was before.

Figure 45 shows the cracking that emerged from the rounded window.



(a)

(b)

(c)

Figure 45 Cracking at rounded window

The load capacity due to the reduced stress concentration increased to 127,272 N (28,000 lbs). This is within the expectations which we outlined in our Phase-I proposal. We also expressed a goal in the Phase-I proposal to be able to increase the load capacity with only a 5% increase in weight. In actuality we reduced the weight slightly. Near the end of the load cycle, the snap-fit did experience extensive non-linear behavior. Evidence of this behavior is shown in Figure 18c. There is also evidence that instead of one crack at each corner the window now experiences at least two cracks at each corner.

A very reassuring observation for designers is that the snap-fit fails very gradually and keeps holding load. Even the heavily damaged section which is shown in Figure 18c was able to still carry 50% of the failure load.

No damage on the radiused cross-member insert was observed.

PRELIMINARY DESIGN OF INNOVATIVE SNAP-FT CONFIGURATIONS FOR THE 40,000 TO 50,000 LBS LOAD CAPACITY RANGE

In the design guidelines we mentioned that a doubler plate would be beneficial in order to increase the load capacity of the snap-fit. An improved configuration is shown in Figure 46.

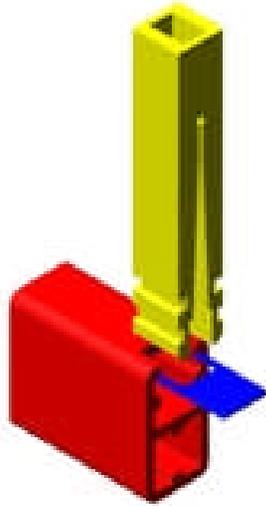


Figure 46 Configuration with underlying metal/ composite doubler (plate)

The blue plate which has been inserted underneath the surface of the red truss member will be bonded to the inside of the top surface and restrain the cracking from occurring. The plate will also help reduce the bending effect into the corner and increase the shear effect. The material for the plate could be steel, but it would be preferred to use a non-corrosive material such as a toughened ceramic or quasi-isotropic carbon or boron composite. Another candidate may be Glare. For compression loading we propose a cage-like configuration.

During the project we generated an idea for a displacement measurement procedure on the snap-fit by means of an optical microscope. This displacement data would be transformed into strain data with appropriate third party software. It will be used as the basis for a presentation to one of the technical societies such as SAMPE (Society of Advanced Materials and Process Engineers) or SEM (Society for Experimental Mechanics)

The load requirements for the complete structural analysis we obtained from AASHTO [7] The analysis was performed with Pro-Mechanica and the results are summarized in Figure 4 7

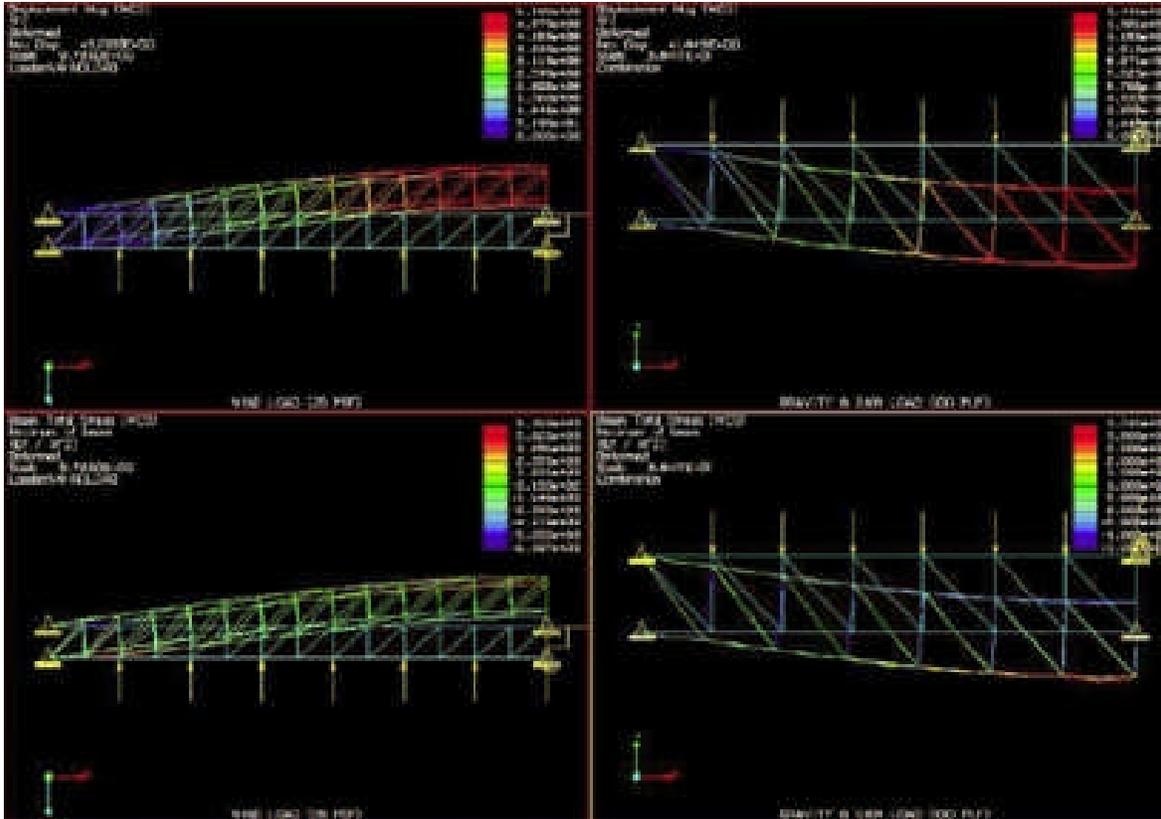


Figure 47 Sign Truss Deflections in Horizontal and Vertical Direction

Following AASHTO specifications, a wind load of 80 mph was assumed. For a 25 ft tall sign structure this translates into a pressure of 25 psf.

This wind pressure was applied to the entire face of the sign truss. For this load case the resulting maximum deflection was 4.94”

The vertical load consisted of the own weight of the sign truss plus a 50 lbs/ linear foot distributed load over the entire free span of 90 ft. The added distributed load accounts for the weight of the signs. For this load case the resulting maximum deflection was 1.37.”

This is L/790 which is well below the L/150 which is referred in section 10-2 of the AAHTO specification.

7. CONCLUSIONS AND RECOMMENDATIONS

In this project we successfully designed, manufactured, and assembled a overhead sign bridge structure.

This structure has been designed for pultrusion, and allows for fastenerless assembly, without the use of tools, with the exception of a few clamps. As such these newly designed structures have the potential to compete on cost with traditional steel construction.

A lightweight composite sign structure with a 90 foot clear span has been designed. This sign truss does not rely on fasteners but on a new “snap joint” which allows for rapid assembly. The “snap joint” which we designed has a load capacity which is well in excess of 22,000 lbs.

The weight of the composite sign truss is less than 1/3rd of the weight of the steel structure. As such it can be installed with light and less expensive lifting equipment.

In summary:

CSSI has designed, constructed and assembled a standard Overhead Highway Sign Bridge – two post truss type out of Fiber Reinforced Polymer (FRP) composite materials utilizing the pultrusion process. The design of the composite sign structure and sign bridge meets all of the requirements of the 1999 Caltrans Standard Specifications and Standard Plans, the 2001 AASHTO Standard Specifications for Structural Supports for Highway Signs, Luminaries and traffic Signals, 4th edition.

The Overhead Sign Bridge – two post truss type, has a span length of ninety (60) feet. The Overhead Sign Truss has a frame depth of ninety-six (96) inches.

All materials and tooling necessary for the fabrication of the Overhead Sign Bridge/Sign have been designed and/ or procured by CSSI. The basic materials are E-Glass for the fiber, and Vinylester for the resin system.

CSSI has developed the conceptual design for the FRP Composite Overhead Sign Bridge, posts, and connection details. Detailed drawings of the Overhead Sign Bridge/Sign Structure have been generated and include selected materials, material properties, fiber architecture, connection details, and assembly details.

CSSI has performed component structural analysis to verify structural performance as required in the 2001 AASHTO Standard Specifications for Highway Signs, Luminaries and traffic Signals, 4th edition, and to verify the structural integrity of the design.

CSSI has produced a 30 ft sign bridge section and a 60 foot sign bridge section. These are ready for field installation.

It is recommended that the lessons learned in this effort be applied to future overhead sign bridge designs. This will lead to structures which require virtually no maintenance, and which don't have the fatigue and cracking issues which plague their aluminum and steel counterparts.

8. REFERENCES

1. J. Batchelor and J.F. Kelly, "The Possible Application of Temporary Composite Structures within the British Rail Network," *Composite Structures* 2 (1984) pp 245-259
2. MoDot, "Signal Mast Arm Failure Investigation," RTD 03-010, July 2003
3. Kaczinski, M. R., Dexter, R.J. and Van Dien, J.P., "Fatigue-Resistant Design of Cantilevered Signal, Sign, and Light Supports, Report to NCHRP, ATLSS Engineering Research Center, Lehigh University, Bethlehem, Pennsylvania
4. Personal Communication with Air Logistics Corporation on repair of fatigued aluminum sign structures for the State of New York
5. W.B. Goldsworthy and C. Hiel, "Composite Structures are a Snap," pp 382-396, Second International Conference on Composites in Infrastructure, H. Saadatmanesh and M.R. Ehsani, Editors, Tucson, AZ 1998.
6. Ronald K. Jurgen, "Smart Cars and Highways go Global," *IEEE Spectrum*, May 1991, pp 26-36.
7. AASHTO, "Standard Specifications for Structural Support for Highway Signs, Luminaires and Traffic Signals, 4th Edition, 2001.
8. John Gizinos, Editor, CALTRANS Standard Plans, July 1999
9. Clem Hiel, "Assembly of 30 ft truss as a demo snap-fit structure." CSSI internal report, February, 2008.
10. Griffel, "Handbook of Formulas for Stress and Strain," Frederick Ungar Publishing Co, New York, 1976.
11. Savin, Holes
12. Jean Avril, "Encyclopedie Vishay d'analyse des Contraintes," Vishay-Micromesures, 1974.
13. Introduction to Stress Analysis by the Photoelastic Coating Technique. Technical Bulletin TDG-1, Photolastic Inc.
14. Zandman, Felix, "Never the Last Journey," Schocken Books, New York, 1995
15. Hiel, C. "Calibration of PS-3A photoelastic sensitive sheet material." CSSI Internal Report, March 2008.
16. Dolan, T.J., Murray, W.M., and Drucker, D.C., "Photoelasticity," in *Handbook of Experimental Stress Analysis*, ed. By M. Hetenyi, John Wiley & Sons, New York, 1950, pp. 826-976.
17. Hobbs, J.W., Burguele, R.L. and Patterson, E.A., "Investigation into the Effect of the Nut Thread run-out on the stress-distribution in a bolt using the Finite Element Method, *Journal of Mechanical Design*, September 2003.
18. Venkatesan, S. and Kinzel, G.L., "Reduction of Stress Concentration in Bolt-Nut Connectors," *Journal of Mechanical Design*, November 2006.
19. Patran, Users Manual, 2007
20. Hiel, C. "Finite Element Analysis of Snap-Fit," CSSI Report, May, 2008
21. Hiel, C. "Test Plan for Snap-Fit Connections," CSSI Internal Report, February, 2008.
22. Lee, D.G., and Cheon, S.S., "Impact Characteristics of Glass Fiber Composites with Respect to Fiber Volume Fraction," *Journal of Composite Materials*," Vol. 35, No1, pp27-55

APPENDIX
CONTRACT 59A0343
DRAWINGS

Drawing	Description
P5007-0001	CONCEPT "I"
P5007-0002	CONCEPT "II", 90 FT BRIDGE
P5007-0003	TENSILE TEST FIXTURE
P5007-0004	CROSS ARM ASSEMBLY
P5007-0005	BRACKET
P5007-0006	WIND BRACE
P5007-0007	TENSILE TEST FIXTURE, TOP CLAMP
P5007-0008	PULTRUSION DIE ASSEMBLY (PROFILE #1)
P5007-0009	PULTRUSION DIE (PROFILE #1)
P5007-0011	PULTRUSION DIE ASSEMBLY (PROFILE #2)
P5007-0012	PULTRUSION ASSEMBLY (PROFILE #1)
P5007-0013	FINISH MANDREL
P5007-0014	DIE SUPPRT BAR
P5007-0015	UPSTREAM TRACK
P5007-0016	PROFILE #1 – PLY SCHEDULE
T5007-0017	WET-OUT TANK WELDMENT
P5007-0020	PULTRUSION SET-UP
P5007-0021	PROFILE #2 – PLY SCHEDULE

T5007-0022 ANCHOR FOR PROFILE #2

P5007-0024 24' SPAN BRIDGE ASSEMBLY

P5007-0026 TOP CHORD "A","B"

P5007-0028 BOTTOM CHORD "C","D"

P5007-0029 VERTICAL

P5007-0030 DIAGONAL

P5007-0031 WIND BRACE

P5007-0035 24' SPAN BRIDGE –OVERHEAD TRUSS ASSEMBLY

P5007-0032 54' SPAN BRIDGE ASSEMBLY

P5007-0033 54' SPAN BRIDGE –OVERHEAD TRUSS ASSEMBLY

P5007-0114 ROUGH MANDREL TYPE "C" FAR SIDE


P5007-0115 ROUGH MANDREL TYPE "C" FAR SIDE

P5007-1004 LOCK PLY-SCHEDULE


T5007-1013 PULTRUSION ASSEMBLY (PROFILE #2)

P5007-1112 LOCK PROFILE

P5007-1113 LOCK PULTRUSION DIE

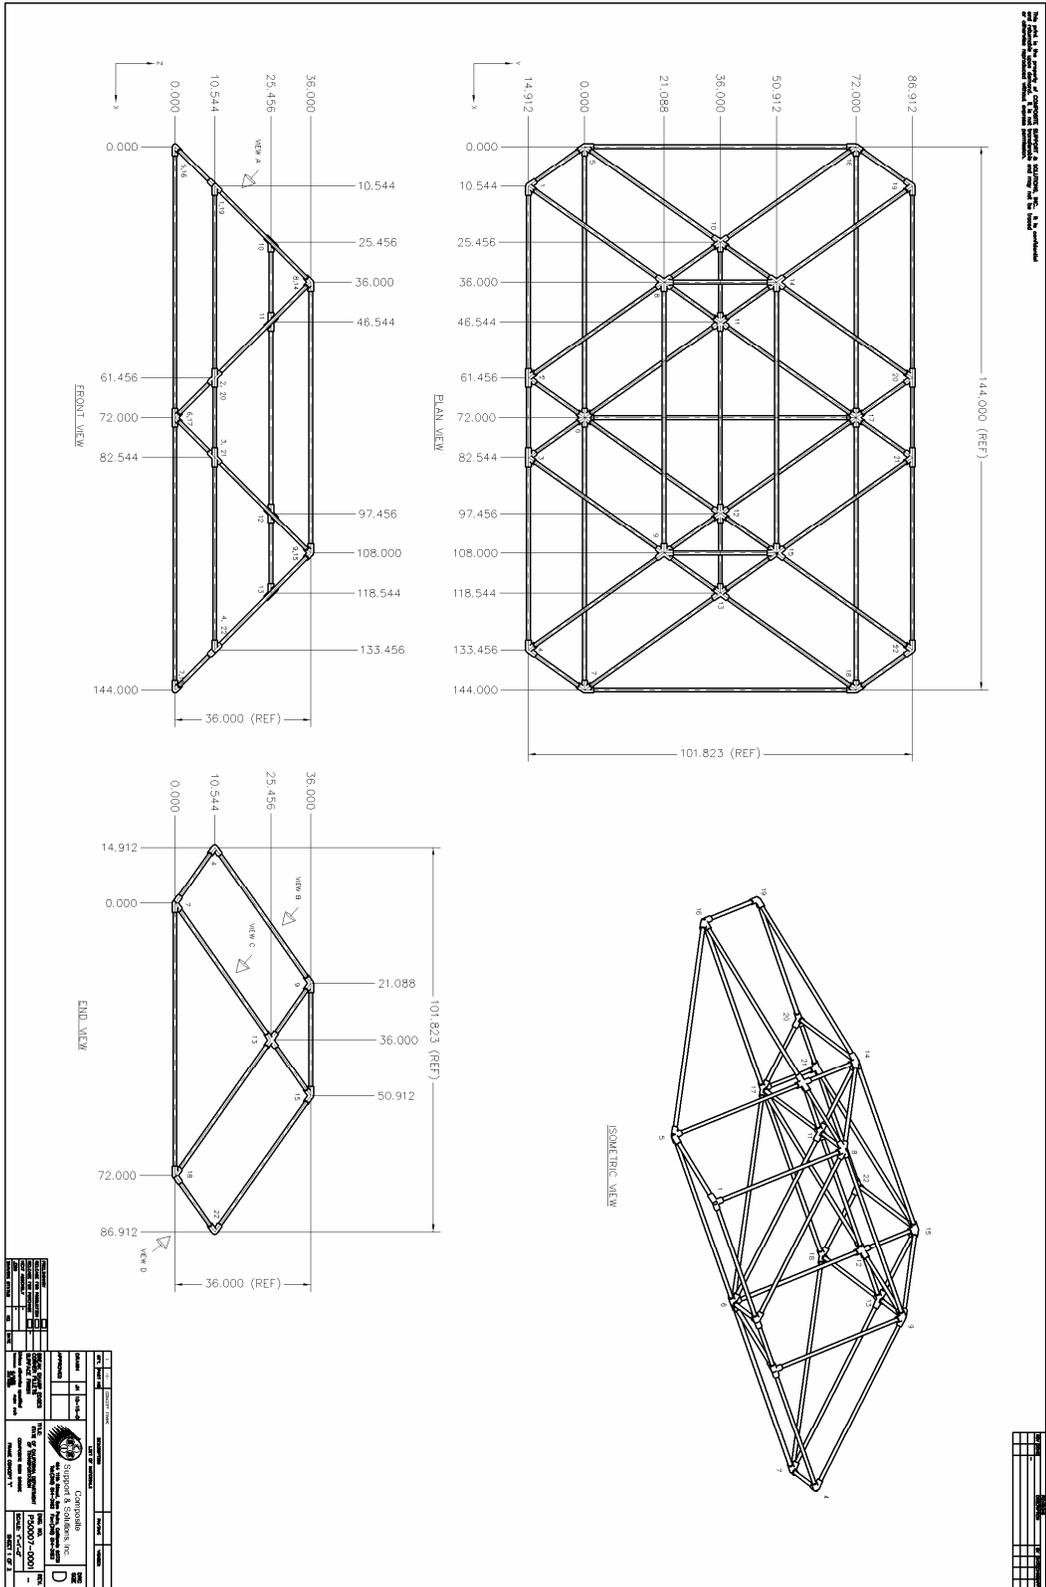

This drawing is the property of Composite Structures & Solutions, Inc. All rights reserved.
 It is to be used only for the project and location specified. No part of this drawing
 or assembly may be reproduced without written permission.

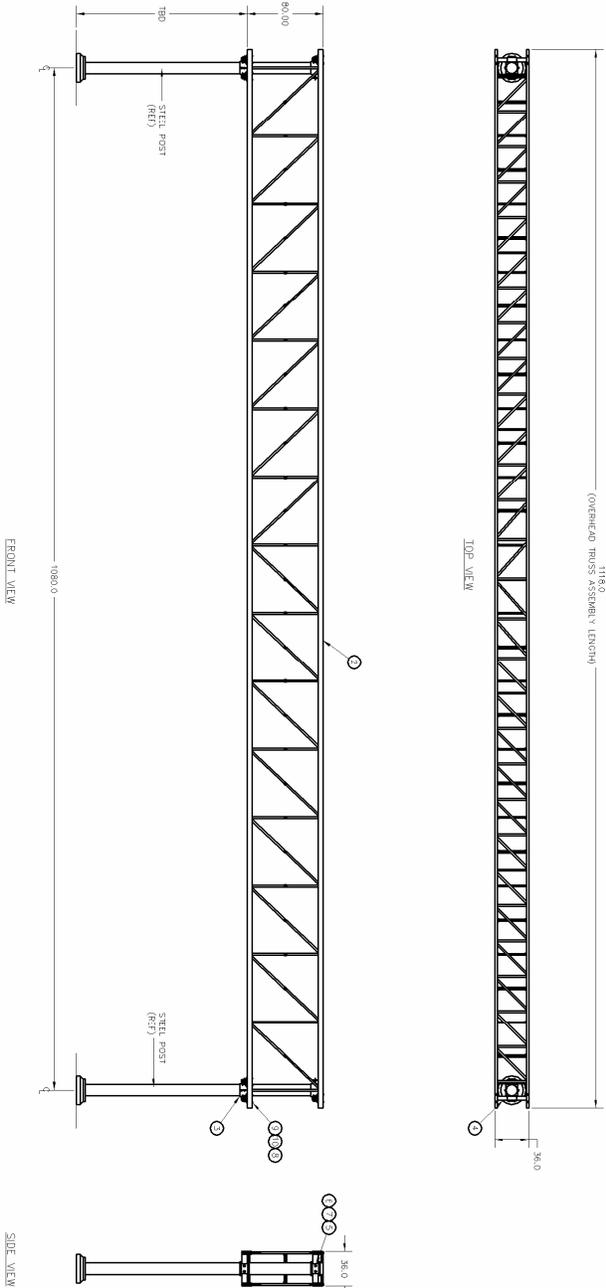

-1-
90' SPAN BRIDGE ASSEMBLY


NOTES
 1. ALL DIMENSIONS ARE IN INCHES

PRELIMINARY


NO.	DESCRIPTION	DATE	BY	CHKD.
1	ISSUED FOR PERMIT	08/15/2023	AS	AS
2	REVISED PER COMMENTS	08/15/2023	AS	AS
3	REVISED PER COMMENTS	08/15/2023	AS	AS
4	REVISED PER COMMENTS	08/15/2023	AS	AS
5	REVISED PER COMMENTS	08/15/2023	AS	AS
6	REVISED PER COMMENTS	08/15/2023	AS	AS
7	REVISED PER COMMENTS	08/15/2023	AS	AS
8	REVISED PER COMMENTS	08/15/2023	AS	AS
9	REVISED PER COMMENTS	08/15/2023	AS	AS
10	REVISED PER COMMENTS	08/15/2023	AS	AS
11	REVISED PER COMMENTS	08/15/2023	AS	AS
12	REVISED PER COMMENTS	08/15/2023	AS	AS
13	REVISED PER COMMENTS	08/15/2023	AS	AS
14	REVISED PER COMMENTS	08/15/2023	AS	AS
15	REVISED PER COMMENTS	08/15/2023	AS	AS
16	REVISED PER COMMENTS	08/15/2023	AS	AS
17	REVISED PER COMMENTS	08/15/2023	AS	AS
18	REVISED PER COMMENTS	08/15/2023	AS	AS
19	REVISED PER COMMENTS	08/15/2023	AS	AS
20	REVISED PER COMMENTS	08/15/2023	AS	AS

Composite Structures & Solutions, Inc.
 10000 Highway 100, Suite 100
 Houston, TX 77036
 Tel: 281-414-1111
 Fax: 281-414-1112
 Email: info@cssi.com
 Website: www.cssi.com


This part is the property of Composite Support & Solutions, Inc. It is intended to be used only for the purpose for which it was designed. No other use is permitted without written permission.

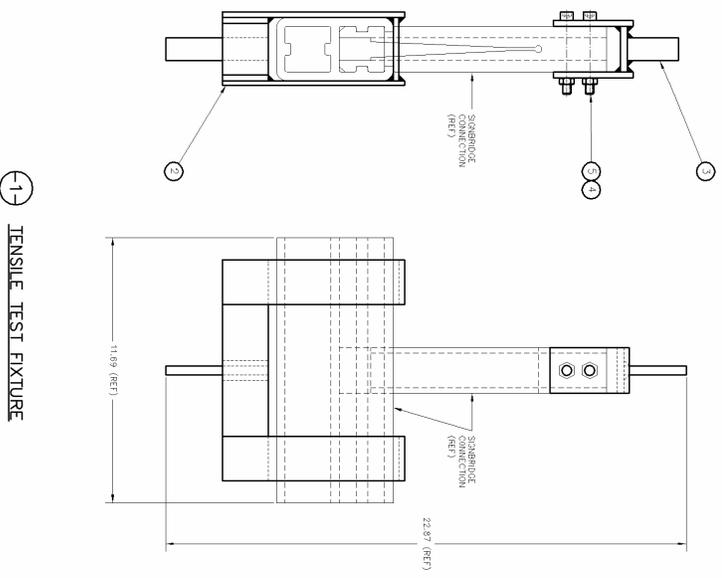

① TENSILE TEST FIXTURE

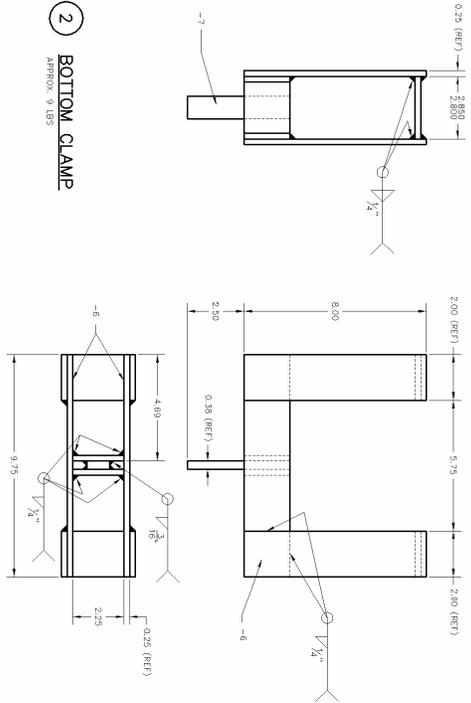

② BOTTOM CLAMP
APPROX. 9 LBS

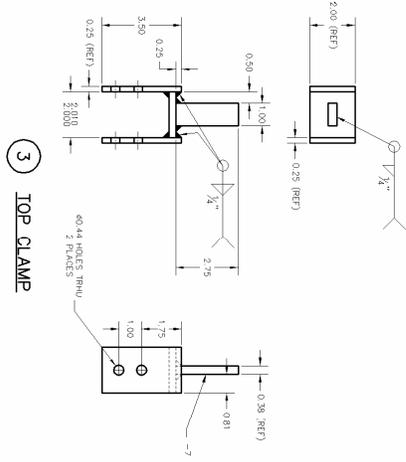

③ TOP CLAMP

PRELIMINARY


REV	DATE	BY	CHKD	DESCRIPTION
1	11/11/2011	WJ	WJ	ISSUED FOR MANUFACTURE
2	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.081 (REF)
3	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
4	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
5	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
6	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
7	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
8	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
9	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
10	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
11	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
12	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
13	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
14	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
15	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
16	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
17	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
18	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
19	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)
20	11/11/2011	WJ	WJ	REVISION: 0.000 (REF) TO 0.25 (REF)

Composite Support & Solutions, Inc.
 10000 W. 10th Street, Suite 100
 Overland Park, KS 66211
 Phone: 913.241.1111
 Fax: 913.241.1112
 Email: info@cs-solutions.com
 Website: www.cs-solutions.com

Not for Construction. Contains Structural & Detailing. See the Structural & Detailing Manual for more information. All dimensions are in inches.

NOTE: DIMENSIONS ARE IN INCHES




(-1-) CROSS ARM ASSEMBLY

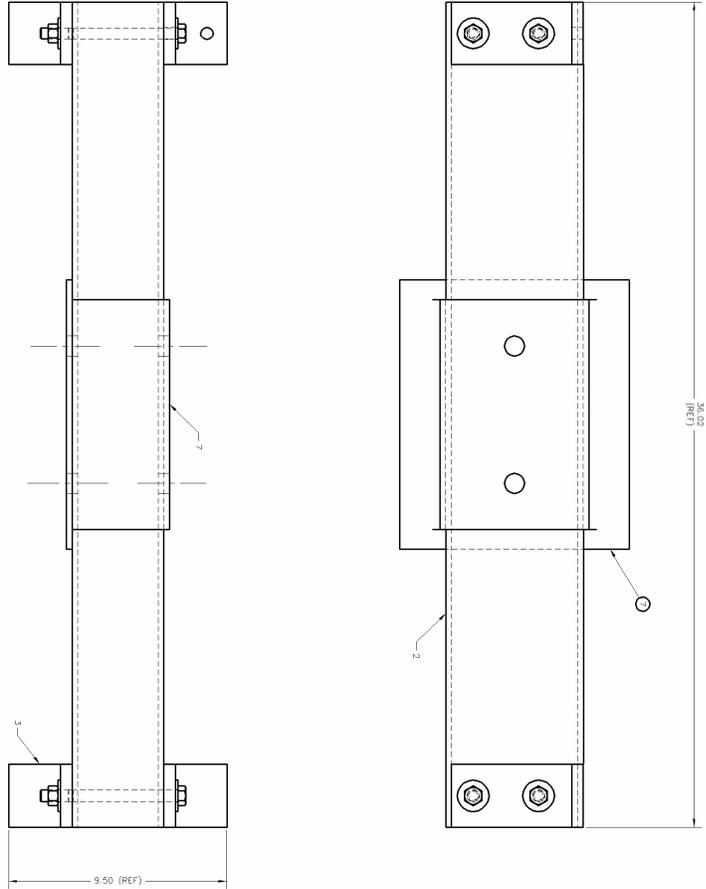

PRELIMINARY

NO.	DESCRIPTION	QTY	UNIT	REVISION
1	CROSS ARM ASSEMBLY	1	EA	1
2	BRACKET	1	EA	1
3	WASHER	2	EA	1
4	BOLT	2	EA	1
5	NUT	2	EA	1
6	WASHER	2	EA	1
7	BOLT	2	EA	1
8	NUT	2	EA	1
9	WASHER	2	EA	1
10	BOLT	2	EA	1
11	NUT	2	EA	1
12	WASHER	2	EA	1
13	BOLT	2	EA	1
14	NUT	2	EA	1
15	WASHER	2	EA	1
16	BOLT	2	EA	1
17	NUT	2	EA	1
18	WASHER	2	EA	1
19	BOLT	2	EA	1
20	NUT	2	EA	1
21	WASHER	2	EA	1
22	BOLT	2	EA	1
23	NUT	2	EA	1
24	WASHER	2	EA	1
25	BOLT	2	EA	1
26	NUT	2	EA	1
27	WASHER	2	EA	1
28	BOLT	2	EA	1
29	NUT	2	EA	1
30	WASHER	2	EA	1
31	BOLT	2	EA	1
32	NUT	2	EA	1
33	WASHER	2	EA	1
34	BOLT	2	EA	1
35	NUT	2	EA	1
36	WASHER	2	EA	1
37	BOLT	2	EA	1
38	NUT	2	EA	1
39	WASHER	2	EA	1
40	BOLT	2	EA	1
41	NUT	2	EA	1
42	WASHER	2	EA	1
43	BOLT	2	EA	1
44	NUT	2	EA	1
45	WASHER	2	EA	1
46	BOLT	2	EA	1
47	NUT	2	EA	1
48	WASHER	2	EA	1
49	BOLT	2	EA	1
50	NUT	2	EA	1
51	WASHER	2	EA	1
52	BOLT	2	EA	1
53	NUT	2	EA	1
54	WASHER	2	EA	1
55	BOLT	2	EA	1
56	NUT	2	EA	1
57	WASHER	2	EA	1
58	BOLT	2	EA	1
59	NUT	2	EA	1
60	WASHER	2	EA	1
61	BOLT	2	EA	1
62	NUT	2	EA	1
63	WASHER	2	EA	1
64	BOLT	2	EA	1
65	NUT	2	EA	1
66	WASHER	2	EA	1
67	BOLT	2	EA	1
68	NUT	2	EA	1
69	WASHER	2	EA	1
70	BOLT	2	EA	1
71	NUT	2	EA	1
72	WASHER	2	EA	1
73	BOLT	2	EA	1
74	NUT	2	EA	1
75	WASHER	2	EA	1
76	BOLT	2	EA	1
77	NUT	2	EA	1
78	WASHER	2	EA	1
79	BOLT	2	EA	1
80	NUT	2	EA	1
81	WASHER	2	EA	1
82	BOLT	2	EA	1
83	NUT	2	EA	1
84	WASHER	2	EA	1
85	BOLT	2	EA	1
86	NUT	2	EA	1
87	WASHER	2	EA	1
88	BOLT	2	EA	1
89	NUT	2	EA	1
90	WASHER	2	EA	1
91	BOLT	2	EA	1
92	NUT	2	EA	1
93	WASHER	2	EA	1
94	BOLT	2	EA	1
95	NUT	2	EA	1
96	WASHER	2	EA	1
97	BOLT	2	EA	1
98	NUT	2	EA	1
99	WASHER	2	EA	1
100	BOLT	2	EA	1
101	NUT	2	EA	1
102	WASHER	2	EA	1
103	BOLT	2	EA	1
104	NUT	2	EA	1
105	WASHER	2	EA	1
106	BOLT	2	EA	1
107	NUT	2	EA	1
108	WASHER	2	EA	1
109	BOLT	2	EA	1
110	NUT	2	EA	1
111	WASHER	2	EA	1
112	BOLT	2	EA	1
113	NUT	2	EA	1
114	WASHER	2	EA	1
115	BOLT	2	EA	1
116	NUT	2	EA	1
117	WASHER	2	EA	1
118	BOLT	2	EA	1
119	NUT	2	EA	1
120	WASHER	2	EA	1
121	BOLT	2	EA	1
122	NUT	2	EA	1
123	WASHER	2	EA	1
124	BOLT	2	EA	1
125	NUT	2	EA	1
126	WASHER	2	EA	1
127	BOLT	2	EA	1
128	NUT	2	EA	1
129	WASHER	2	EA	1
130	BOLT	2	EA	1
131	NUT	2	EA	1
132	WASHER	2	EA	1
133	BOLT	2	EA	1
134	NUT	2	EA	1
135	WASHER	2	EA	1
136	BOLT	2	EA	1
137	NUT	2	EA	1
138	WASHER	2	EA	1
139	BOLT	2	EA	1
140	NUT	2	EA	1
141	WASHER	2	EA	1
142	BOLT	2	EA	1
143	NUT	2	EA	1
144	WASHER	2	EA	1
145	BOLT	2	EA	1
146	NUT	2	EA	1
147	WASHER	2	EA	1
148	BOLT	2	EA	1
149	NUT	2	EA	1
150	WASHER	2	EA	1

This part is the property of Composite Structures, Inc. It is intended for use only in the aircraft for which it was designed. It is not to be used in any other aircraft without the express written permission of Composite Structures, Inc.

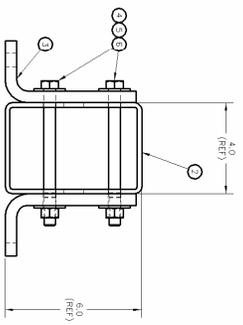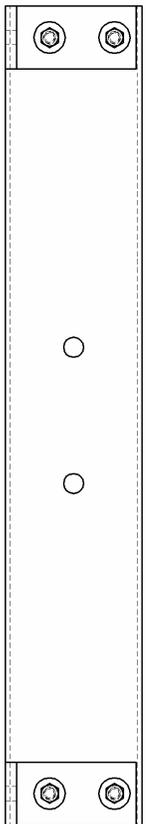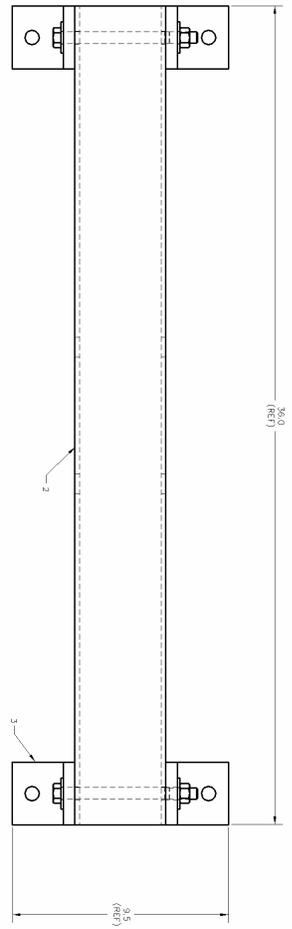


①-1 CROSS ARM ASSEMBLY

PRELIMINARY



REV	DATE	DESCRIPTION	BY	CHKD
1		ISSUED FOR CONSTRUCTION		

<p>Composite Structures, Inc. 10000 W. 10th Street Denver, CO 80202 Tel: 303.751.1000 Fax: 303.751.1001 www.composite-structures.com</p>	<p>Part No. P5007-0004-1 Rev. 1</p>
--	---

This part is the property of Composite Structures & Solutions, Inc. It is intended to be used only for the purpose of manufacturing the product identified on this drawing. It is not to be used for any other purpose.

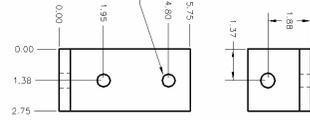

3 ANGLE
MATERIAL COMPONENT

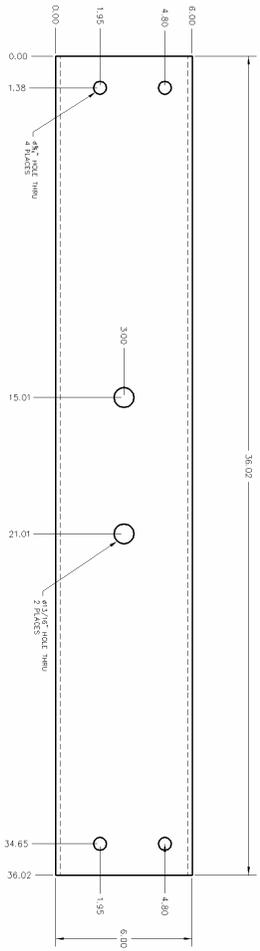



2 RECTANGLE 4"x6"
MATERIAL COMPONENT



REV	DATE	BY	CHKD	DESCRIPTION
1	08/11/2011	WJ	WJ	ISSUE FOR MANUFACTURE
2	08/11/2011	WJ	WJ	REVISION
3	08/11/2011	WJ	WJ	REVISION
4	08/11/2011	WJ	WJ	REVISION
5	08/11/2011	WJ	WJ	REVISION
6	08/11/2011	WJ	WJ	REVISION
7	08/11/2011	WJ	WJ	REVISION
8	08/11/2011	WJ	WJ	REVISION
9	08/11/2011	WJ	WJ	REVISION
10	08/11/2011	WJ	WJ	REVISION

Material	Material	Composite Structures & Solutions, Inc.
Part Name	Part Name	P5007-0004
Part Number	Part Number	00000000
Part Description	Part Description	RECTANGLE 4"x6"
Part Location	Part Location	00000000
Part Status	Part Status	00000000
Part Drawing	Part Drawing	00000000
Part Revision	Part Revision	00000000
Part Date	Part Date	08/11/2011
Part Author	Part Author	WJ
Part Checker	Part Checker	WJ
Part Engineer	Part Engineer	WJ
Part Designer	Part Designer	WJ
Part Drafter	Part Drafter	WJ
Part Approver	Part Approver	WJ

This drawing is the property of Composite Structures & Solutions, Inc. It is to be used only for the project and location specified. It is not to be used for any other project or location without the written consent of Composite Structures & Solutions, Inc.

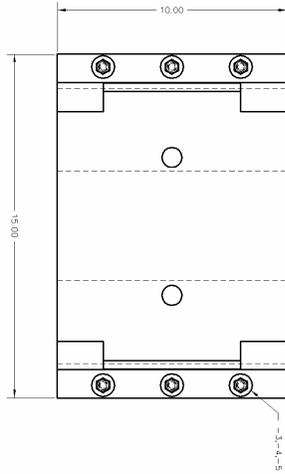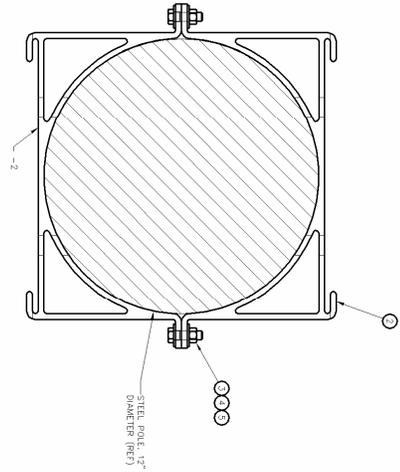

1 MOUNTING BRACKET ASSEMBLY

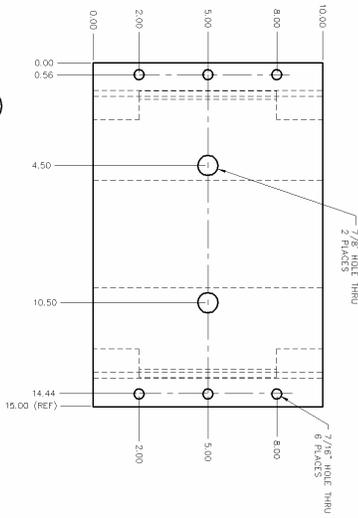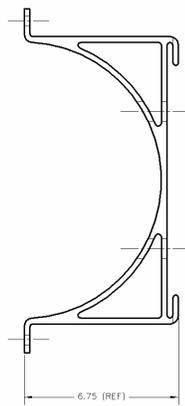


2 BRACKET
1/8" COMP. STAINL.


PRELIMINARY

REV	DATE	DESCRIPTION	BY	CHKD
1	08/11/2011	ISSUED FOR CONSTRUCTION	MS	MS
2	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
3	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
4	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
5	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
6	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
7	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
8	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
9	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS
10	08/11/2011	REVISED TO ADD 1/8" COMP. STAINL.	MS	MS

Composite Structures & Solutions, Inc.
 10000 S. 10th Street, Suite 100
 Tulsa, Oklahoma 74116
 Phone: (918) 438-1111
 Fax: (918) 438-1112
 Email: info@cs-solutions.com
 Website: www.cs-solutions.com

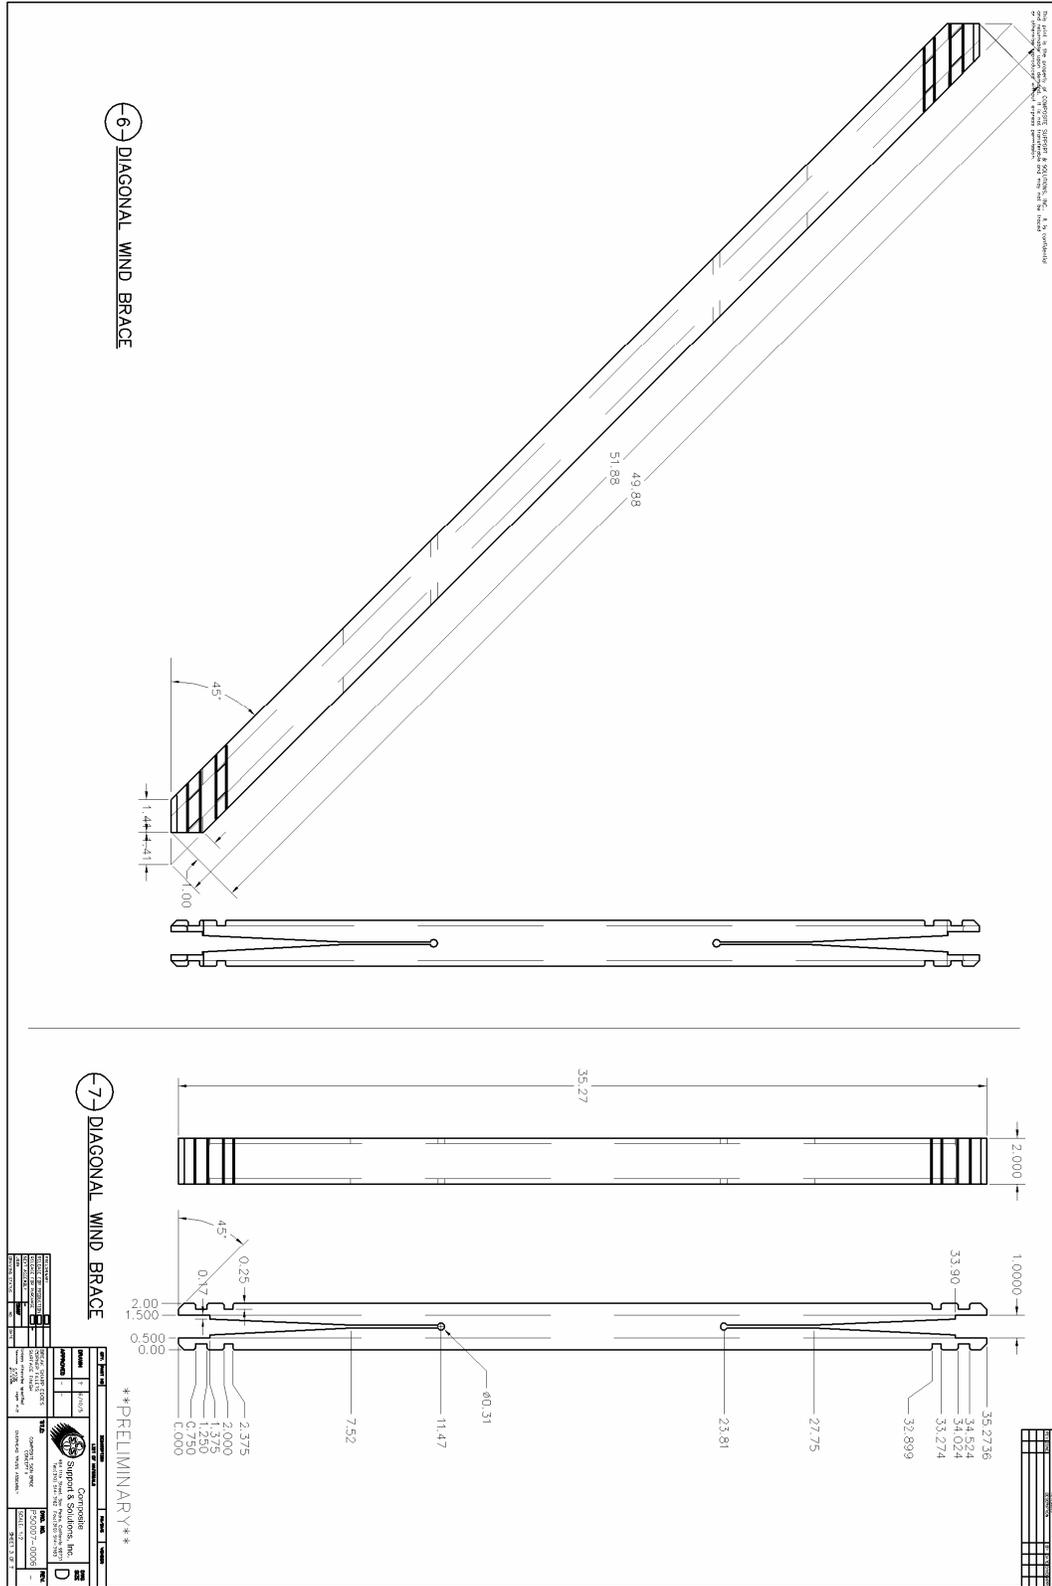

This part is the property of Composite Structures & Solutions, Inc. It is to be used only for the purpose intended and is not to be used for any other purpose.

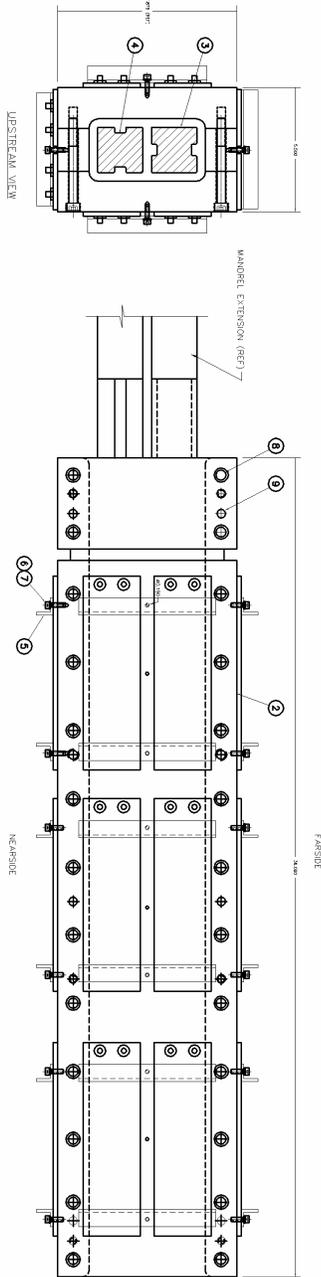


PULTRUSION DIE ASSEMBLY (PROFILE #1)


** PRELIMINARY **

REV	DATE	DESCRIPTION	BY	CHKD
1	08/11/2011	ISSUE FOR MANUFACTURE	W. J. BROWN	J. L. BROWN

Composite Structures & Solutions, Inc. 10000 Highway 100 Houston, TX 77036-1000 Phone: 281-291-1000 Fax: 281-291-1001 Email: sales@cs-s.com	P5007-0008 PULTRUSION DIE ASSEMBLY (PROFILE #1)
--	--

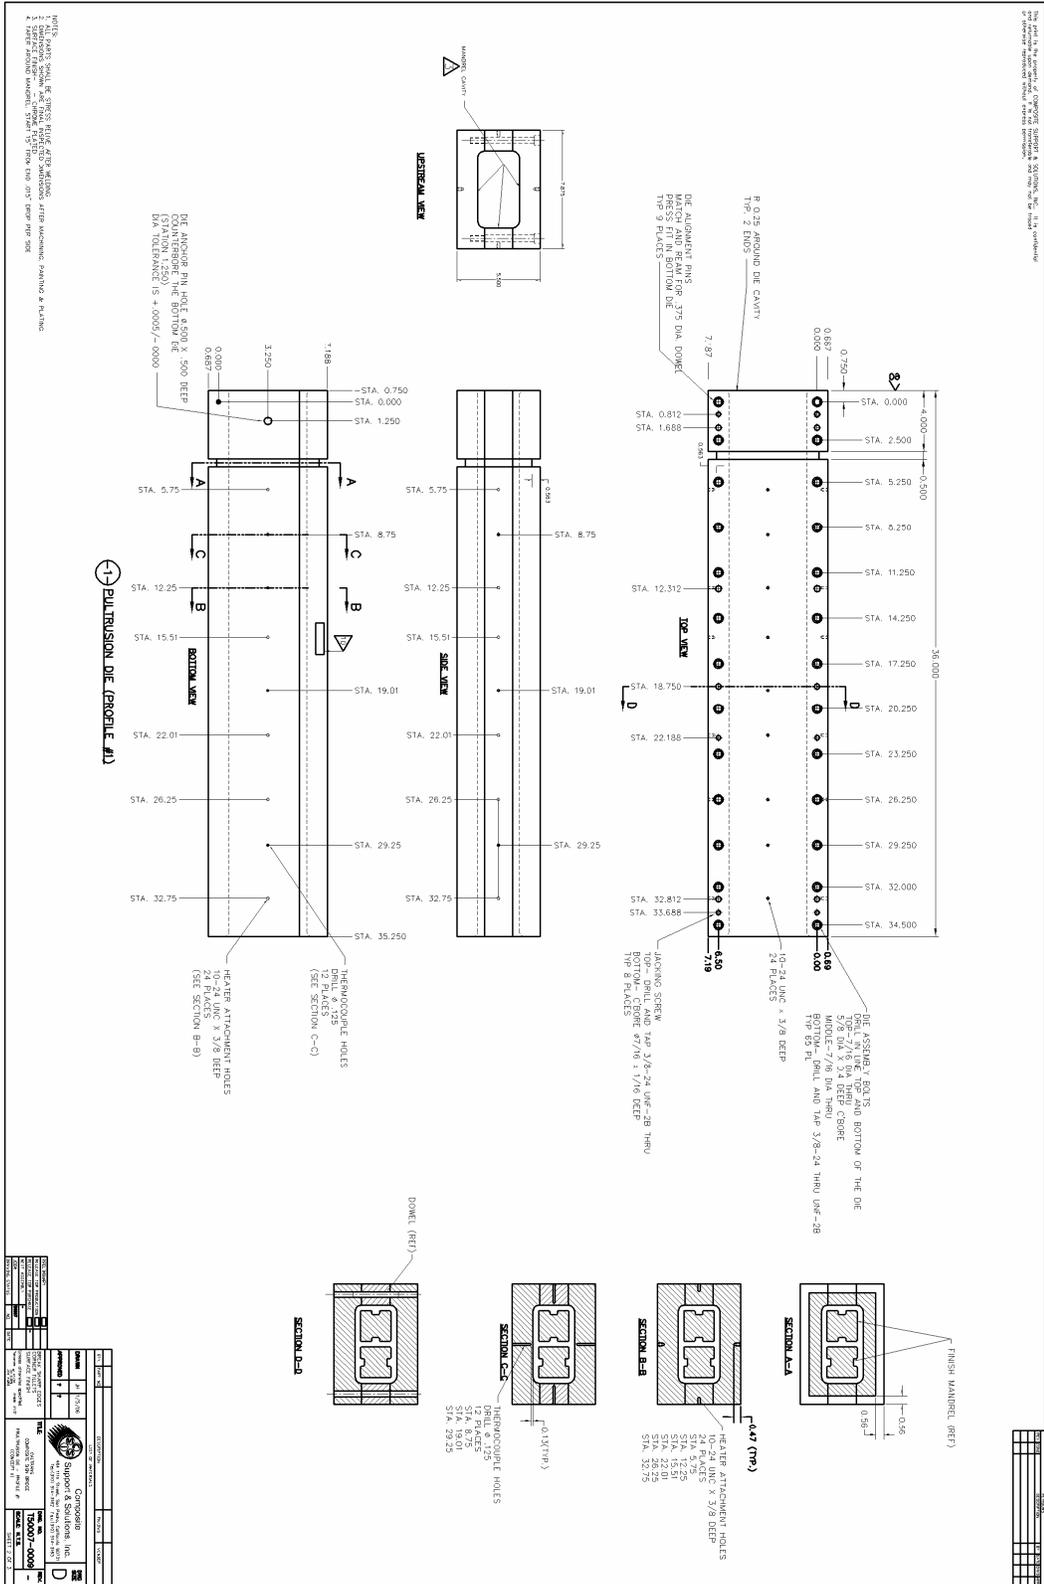

This part is a component of Composite Support & Solutions, Inc. and is not to be used in any other application without the written permission of Composite Support & Solutions, Inc.

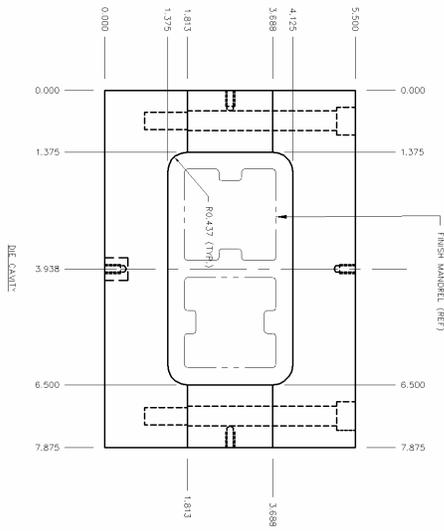

1.375


REV	DATE	BY	CHKD	DESCRIPTION
1	08/11/2011
2	08/11/2011
3	08/11/2011
4	08/11/2011
5	08/11/2011
6	08/11/2011
7	08/11/2011
8	08/11/2011
9	08/11/2011
10	08/11/2011
11	08/11/2011
12	08/11/2011
13	08/11/2011
14	08/11/2011
15	08/11/2011
16	08/11/2011
17	08/11/2011
18	08/11/2011
19	08/11/2011
20	08/11/2011
21	08/11/2011
22	08/11/2011
23	08/11/2011
24	08/11/2011
25	08/11/2011
26	08/11/2011
27	08/11/2011
28	08/11/2011
29	08/11/2011
30	08/11/2011
31	08/11/2011
32	08/11/2011
33	08/11/2011
34	08/11/2011
35	08/11/2011
36	08/11/2011
37	08/11/2011
38	08/11/2011
39	08/11/2011
40	08/11/2011
41	08/11/2011
42	08/11/2011
43	08/11/2011
44	08/11/2011
45	08/11/2011
46	08/11/2011
47	08/11/2011
48	08/11/2011
49	08/11/2011
50	08/11/2011
51	08/11/2011
52	08/11/2011
53	08/11/2011
54	08/11/2011
55	08/11/2011
56	08/11/2011
57	08/11/2011
58	08/11/2011
59	08/11/2011
60	08/11/2011
61	08/11/2011
62	08/11/2011
63	08/11/2011
64	08/11/2011
65	08/11/2011
66	08/11/2011
67	08/11/2011
68	08/11/2011
69	08/11/2011
70	08/11/2011
71	08/11/2011
72	08/11/2011
73	08/11/2011
74	08/11/2011
75	08/11/2011
76	08/11/2011
77	08/11/2011
78	08/11/2011
79	08/11/2011
80	08/11/2011
81	08/11/2011
82	08/11/2011
83	08/11/2011
84	08/11/2011
85	08/11/2011
86	08/11/2011
87	08/11/2011
88	08/11/2011
89	08/11/2011
90	08/11/2011
91	08/11/2011
92	08/11/2011
93	08/11/2011
94	08/11/2011
95	08/11/2011
96	08/11/2011
97	08/11/2011
98	08/11/2011
99	08/11/2011
100	08/11/2011

NOTES: DIE SPECIFICATION

1. INTERPRET DRAWING PER ANSI Y14.5-1982.
2. MATERIAL 4130, 4140 OR 4340 OR A1A1-P20. IF 4130, 4140 OR 4340 IS USED, HEAT TREAT TO Rc 32-35 BEFORE MACHINING. IF A1A1-P20 IS USED, HEAT TREAT TO Rc 38-42 BEFORE MACHINING. IF WELDED, ALL WELDS ARE SOLID, CONTINUOUS, NON-POROUS (AIR TIGHT). WELDED PARTS TO BE STRESS RELIEVED AFTER WELDING AND ALL PARTS TO BE PRE HARDENED TO Rc 38-42 BEFORE MACHINING. WELDS INDICATED ARE TO BE AS LONG AS WELDING ACCESS WILL PERMIT.
4. UNLESS OTHERWISE SPECIFIED TOLERANCE ON .XXX TO BE ±005 NON-ACCUMULATIVE.
5. DIE & MANDREL SURFACE FINISH TO BE 8 MICRONS OR BETTER BEFORE PLATING.
6. ALL DIE CAVITY SURFACES AND DIMENSIONS ARE AFTER PLATING AND GRINDING.
7. DIE CAVITY MATING SURFACES ARE TO BE PARALLEL AND/OR PERPENDICULAR TO DATUMS WITHIN .002" OVER ENTIRE SURFACE.
8. -HARD CHROME PLATING ON ALL DIE CAVITY AND MANDREL SURFACES TO BE .0015 - .0025 THICK AFTER GRINDING.
-REGRIND AND/OR POLISH CHROME SURFACE FINISH TO 8 MICRONS OR BETTER.
9. BREAK ALL SHARP EDGES.
CHAMFER ALL THREADED HOLES AT MATING SURFACES 45° x .03
10. STAMP TOOL NUMBER AND DETAIL NUMBER IN INDICATED AREA 50007-0009
11. ALL UPSTREAM/DOWNSTREAM (IN AND OUT) DIE RADIUS SHALL BE .25 (STANDARD).
12. ALL DIMENSIONS ARE IN INCHES.

 Composite Superior & Sullivan, Inc. 1000 Superior Blvd. Superior, WI 54985							
Part No. 50007-0009 Description STAMP		Material 4130 Heat Treat 32-35		Finish 8 Plating CHROME		Quantity 1 Unit EA	
Drawing No. 75000-0009 Revision 1 Date 11/11/09				Drawing No. 75000-0009 Revision 1 Date 11/11/09			

Part of the Agreement of Composite Materials & Solutions, Inc. with the customer.
 All dimensions are in inches unless otherwise specified.
 All tolerances are unless otherwise specified.

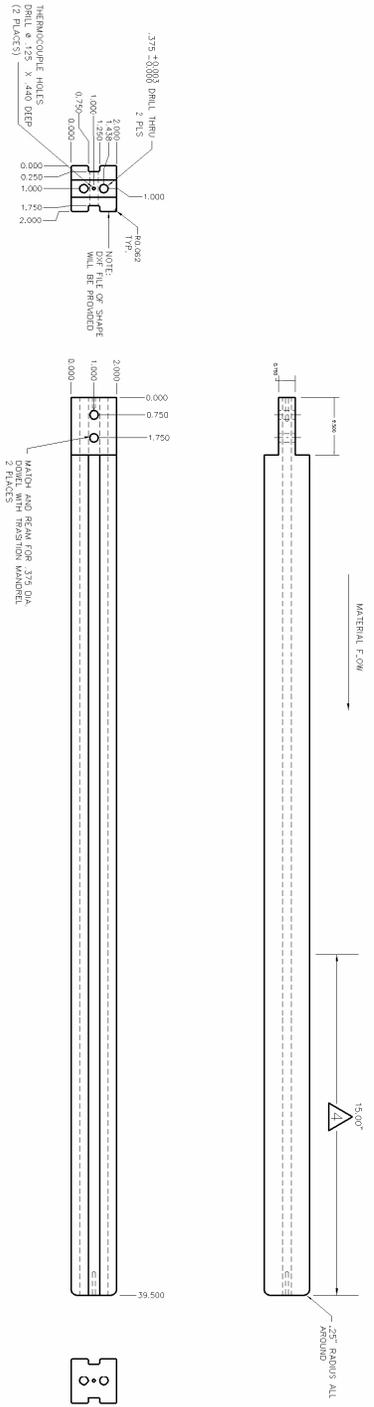


- NOTES:
1. ALL PARTS SHALL BE STRESS RELIEF AFTER MACHINING.
 2. SURFACE FINISH - CHROME PLATED.
 3. SURFACE FINISH - CHROME PLATED.
 4. TAPER AROUND MANDREL START 15" FROM END 0.05" DROP PER SIDE.

① FINISH MANDREL

REV	DATE	DESCRIPTION	BY	CHKD
1	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
2	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
3	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
4	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
5	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
6	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
7	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
8	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
9	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ
10	08/11/10	ISSUE FOR MANUFACTURE	WJ	WJ

Composite Support & Solutions, Inc.
 10000 W. 10th Ave. Suite 100
 Denver, CO 80231
 Phone: 303.755.1100
 Fax: 303.755.1101
 Email: info@composite-support.com
 Website: www.composite-support.com

This part is a property of Composite Support & Solutions, Inc. All rights reserved. No part of this document may be reproduced without written permission.

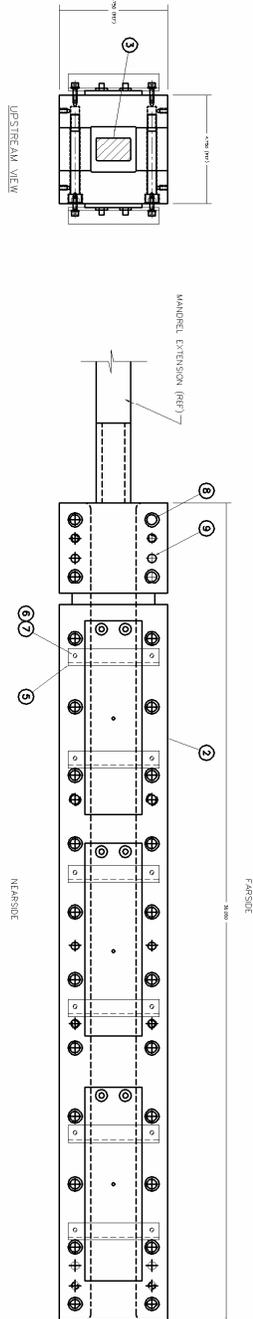


1-1 PULTRUSION DIE ASSEMBLY (PROFILE #2)

PRELIMINARY


NO.	DESCRIPTION	QTY	UNIT	REVISION
1	FRONT VIEW	1	VIEW	1
2	FRONT VIEW	1	VIEW	1
3	FRONT VIEW	1	VIEW	1
4	FRONT VIEW	1	VIEW	1
5	FRONT VIEW	1	VIEW	1
6	FRONT VIEW	1	VIEW	1
7	FRONT VIEW	1	VIEW	1
8	FRONT VIEW	1	VIEW	1
9	FRONT VIEW	1	VIEW	1
10	FRONT VIEW	1	VIEW	1
11	FRONT VIEW	1	VIEW	1
12	FRONT VIEW	1	VIEW	1
13	FRONT VIEW	1	VIEW	1
14	FRONT VIEW	1	VIEW	1
15	FRONT VIEW	1	VIEW	1
16	FRONT VIEW	1	VIEW	1
17	FRONT VIEW	1	VIEW	1
18	FRONT VIEW	1	VIEW	1
19	FRONT VIEW	1	VIEW	1
20	FRONT VIEW	1	VIEW	1
21	FRONT VIEW	1	VIEW	1
22	FRONT VIEW	1	VIEW	1
23	FRONT VIEW	1	VIEW	1
24	FRONT VIEW	1	VIEW	1
25	FRONT VIEW	1	VIEW	1
26	FRONT VIEW	1	VIEW	1
27	FRONT VIEW	1	VIEW	1
28	FRONT VIEW	1	VIEW	1
29	FRONT VIEW	1	VIEW	1
30	FRONT VIEW	1	VIEW	1
31	FRONT VIEW	1	VIEW	1
32	FRONT VIEW	1	VIEW	1
33	FRONT VIEW	1	VIEW	1
34	FRONT VIEW	1	VIEW	1
35	FRONT VIEW	1	VIEW	1
36	FRONT VIEW	1	VIEW	1
37	FRONT VIEW	1	VIEW	1
38	FRONT VIEW	1	VIEW	1
39	FRONT VIEW	1	VIEW	1
40	FRONT VIEW	1	VIEW	1
41	FRONT VIEW	1	VIEW	1
42	FRONT VIEW	1	VIEW	1
43	FRONT VIEW	1	VIEW	1
44	FRONT VIEW	1	VIEW	1
45	FRONT VIEW	1	VIEW	1
46	FRONT VIEW	1	VIEW	1
47	FRONT VIEW	1	VIEW	1
48	FRONT VIEW	1	VIEW	1
49	FRONT VIEW	1	VIEW	1
50	FRONT VIEW	1	VIEW	1
51	FRONT VIEW	1	VIEW	1
52	FRONT VIEW	1	VIEW	1
53	FRONT VIEW	1	VIEW	1
54	FRONT VIEW	1	VIEW	1
55	FRONT VIEW	1	VIEW	1
56	FRONT VIEW	1	VIEW	1
57	FRONT VIEW	1	VIEW	1
58	FRONT VIEW	1	VIEW	1
59	FRONT VIEW	1	VIEW	1
60	FRONT VIEW	1	VIEW	1
61	FRONT VIEW	1	VIEW	1
62	FRONT VIEW	1	VIEW	1
63	FRONT VIEW	1	VIEW	1
64	FRONT VIEW	1	VIEW	1
65	FRONT VIEW	1	VIEW	1
66	FRONT VIEW	1	VIEW	1
67	FRONT VIEW	1	VIEW	1
68	FRONT VIEW	1	VIEW	1
69	FRONT VIEW	1	VIEW	1
70	FRONT VIEW	1	VIEW	1
71	FRONT VIEW	1	VIEW	1
72	FRONT VIEW	1	VIEW	1
73	FRONT VIEW	1	VIEW	1
74	FRONT VIEW	1	VIEW	1
75	FRONT VIEW	1	VIEW	1
76	FRONT VIEW	1	VIEW	1
77	FRONT VIEW	1	VIEW	1
78	FRONT VIEW	1	VIEW	1
79	FRONT VIEW	1	VIEW	1
80	FRONT VIEW	1	VIEW	1
81	FRONT VIEW	1	VIEW	1
82	FRONT VIEW	1	VIEW	1
83	FRONT VIEW	1	VIEW	1
84	FRONT VIEW	1	VIEW	1
85	FRONT VIEW	1	VIEW	1
86	FRONT VIEW	1	VIEW	1
87	FRONT VIEW	1	VIEW	1
88	FRONT VIEW	1	VIEW	1
89	FRONT VIEW	1	VIEW	1
90	FRONT VIEW	1	VIEW	1
91	FRONT VIEW	1	VIEW	1
92	FRONT VIEW	1	VIEW	1
93	FRONT VIEW	1	VIEW	1
94	FRONT VIEW	1	VIEW	1
95	FRONT VIEW	1	VIEW	1
96	FRONT VIEW	1	VIEW	1
97	FRONT VIEW	1	VIEW	1
98	FRONT VIEW	1	VIEW	1
99	FRONT VIEW	1	VIEW	1
100	FRONT VIEW	1	VIEW	1

This part is a component of Composite Support & Solutions, Inc. and is not to be used or otherwise reproduced without written permission.

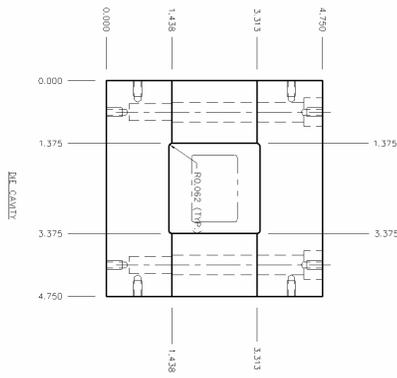

REV	DATE	BY	CHKD	DESCRIPTION
1				ISSUE FOR MANUFACTURE
2				REVISION
3				REVISION
4				REVISION
5				REVISION
6				REVISION
7				REVISION
8				REVISION
9				REVISION
10				REVISION
11				REVISION
12				REVISION
13				REVISION
14				REVISION
15				REVISION
16				REVISION
17				REVISION
18				REVISION
19				REVISION
20				REVISION
21				REVISION
22				REVISION
23				REVISION
24				REVISION
25				REVISION
26				REVISION
27				REVISION
28				REVISION
29				REVISION
30				REVISION
31				REVISION
32				REVISION
33				REVISION
34				REVISION
35				REVISION
36				REVISION
37				REVISION
38				REVISION
39				REVISION
40				REVISION
41				REVISION
42				REVISION
43				REVISION
44				REVISION
45				REVISION
46				REVISION
47				REVISION
48				REVISION
49				REVISION
50				REVISION
51				REVISION
52				REVISION
53				REVISION
54				REVISION
55				REVISION
56				REVISION
57				REVISION
58				REVISION
59				REVISION
60				REVISION
61				REVISION
62				REVISION
63				REVISION
64				REVISION
65				REVISION
66				REVISION
67				REVISION
68				REVISION
69				REVISION
70				REVISION
71				REVISION
72				REVISION
73				REVISION
74				REVISION
75				REVISION
76				REVISION
77				REVISION
78				REVISION
79				REVISION
80				REVISION
81				REVISION
82				REVISION
83				REVISION
84				REVISION
85				REVISION
86				REVISION
87				REVISION
88				REVISION
89				REVISION
90				REVISION
91				REVISION
92				REVISION
93				REVISION
94				REVISION
95				REVISION
96				REVISION
97				REVISION
98				REVISION
99				REVISION
100				REVISION

This part is the property of Precision Die Casting, Inc. It is to be used only for the purpose intended and is not to be resold, copied, or otherwise used without the express written consent of Precision Die Casting, Inc.

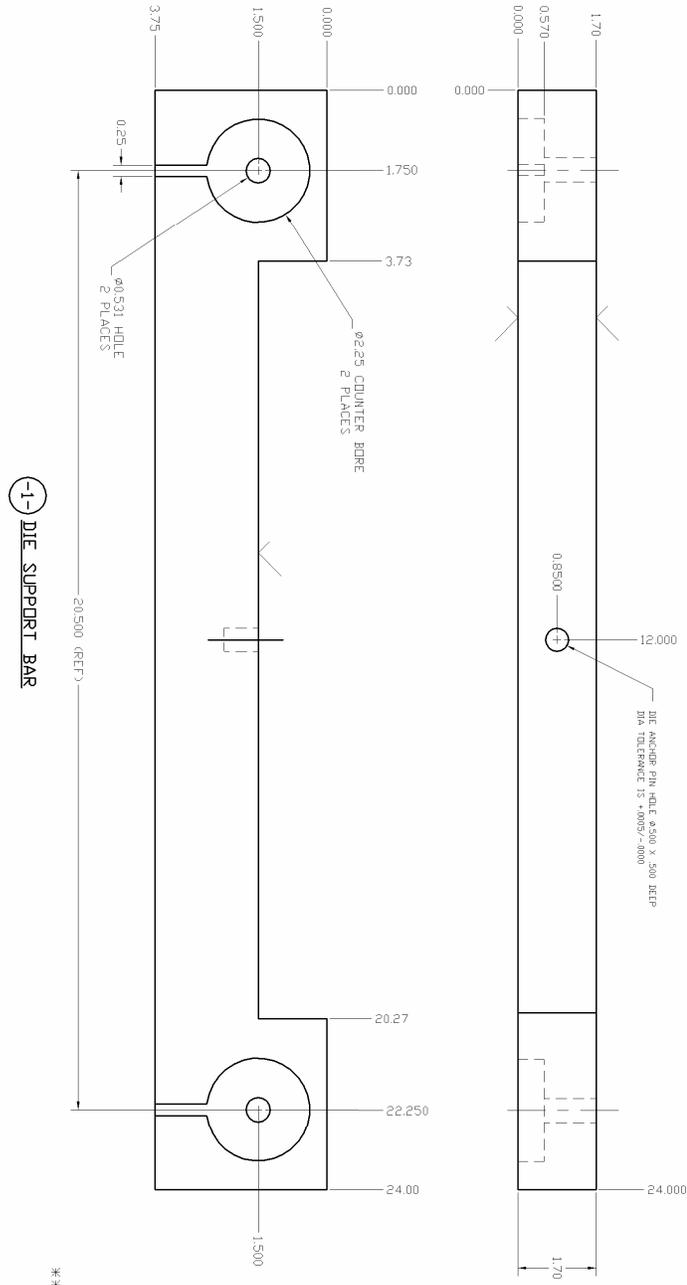


1- DIE SUPPORT BAR

PRELIMINARY


DATE	BY	CHKD	APP'D	DESCRIPTION
08/11/2014	J. S. [Signature]	J. S. [Signature]	J. S. [Signature]	REVISED
08/11/2014	J. S. [Signature]	J. S. [Signature]	J. S. [Signature]	REVISED
08/11/2014	J. S. [Signature]	J. S. [Signature]	J. S. [Signature]	REVISED
08/11/2014	J. S. [Signature]	J. S. [Signature]	J. S. [Signature]	REVISED

Precision Die Casting, Inc. 10000 W. 10th St. Overland Park, MO 66204 Tel: 816-875-1100 Fax: 816-875-1101 www.precisiondiecasting.com	Customer: Support & Solutions, Inc. 10000 W. 10th St. Overland Park, MO 66204 Tel: 816-875-1100 Fax: 816-875-1101 www.precisiondiecasting.com
Part Name: Die Support Bar	Part Number: P5007-0014
Drawing No.: 08/11/2014	Revision: 1


Part of the contract of Composite Structures & Solutions, Inc. is to provide design services for the construction of the above described structure. The design is preliminary and subject to change without notice.

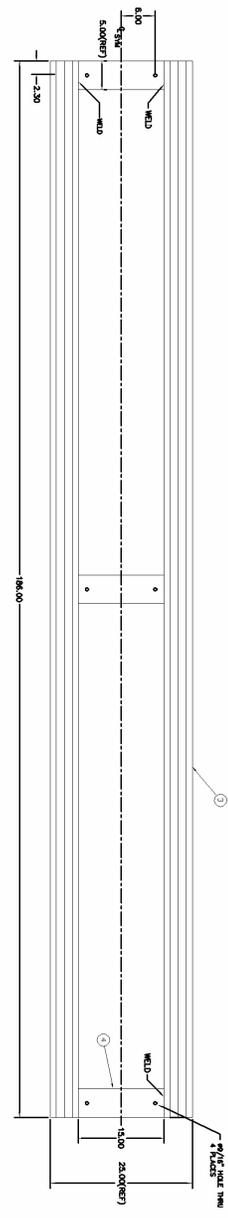

-1- DOWNSTREAM TRACK

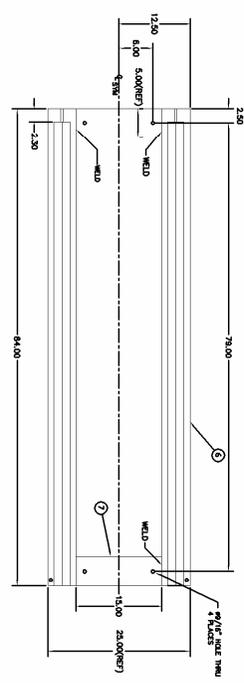

-2- UPSTREAM TRACK

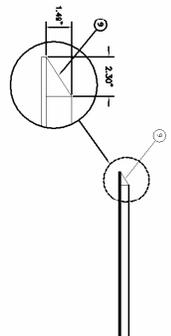

** PRELIMINARY **

NO.	DESCRIPTION	QTY	UNIT	PRICE	TOTAL
1	STEEL TRACK	1	LINEAR FOOT	100.00	100.00
2	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
3	WELD	1	LINEAR FOOT	10.00	10.00
4	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
5	WELD	1	LINEAR FOOT	10.00	10.00
6	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
7	WELD	1	LINEAR FOOT	10.00	10.00
8	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
9	WELD	1	LINEAR FOOT	10.00	10.00
10	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
11	WELD	1	LINEAR FOOT	10.00	10.00
12	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
13	WELD	1	LINEAR FOOT	10.00	10.00
14	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
15	WELD	1	LINEAR FOOT	10.00	10.00
16	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
17	WELD	1	LINEAR FOOT	10.00	10.00
18	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
19	WELD	1	LINEAR FOOT	10.00	10.00
20	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
21	WELD	1	LINEAR FOOT	10.00	10.00
22	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
23	WELD	1	LINEAR FOOT	10.00	10.00
24	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
25	WELD	1	LINEAR FOOT	10.00	10.00
26	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
27	WELD	1	LINEAR FOOT	10.00	10.00
28	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
29	WELD	1	LINEAR FOOT	10.00	10.00
30	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
31	WELD	1	LINEAR FOOT	10.00	10.00
32	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
33	WELD	1	LINEAR FOOT	10.00	10.00
34	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
35	WELD	1	LINEAR FOOT	10.00	10.00
36	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
37	WELD	1	LINEAR FOOT	10.00	10.00
38	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
39	WELD	1	LINEAR FOOT	10.00	10.00
40	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
41	WELD	1	LINEAR FOOT	10.00	10.00
42	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
43	WELD	1	LINEAR FOOT	10.00	10.00
44	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
45	WELD	1	LINEAR FOOT	10.00	10.00
46	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
47	WELD	1	LINEAR FOOT	10.00	10.00
48	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00
49	WELD	1	LINEAR FOOT	10.00	10.00
50	STEEL ANGLE	1	LINEAR FOOT	50.00	50.00

Composite Structures & Solutions, Inc.
 10000 W. 10th Street, Suite 100
 Overland Park, KS 66211
 Phone: 913-666-1111
 Fax: 913-666-1112
 Email: info@cs-s.com


This print is the property of Composite Support & Solutions, Inc. It is confidential and may not be used or otherwise reproduced without express permission.

*** COMPOSITE SUPPORT & SOLUTIONS INC. CONFIDENTIAL ***

MATERIAL LEGEND

MAT TYPE	REINFORCEMENT TYPE	COMPOSITION WEIGHT % ORIENTATION	WEIGHT (gr/ft ²) (oz/ft ²)	REGULATION (NUMBER / STYLE)
A	VEL	100	.1	2014 RESINAY
B	MAT	CONTINUOUS	305	1.02/FT2 MAT
C	O/WOVEN/O/90	50/25/25	1094	1.50/WR 18 765

NOTE: WR-765 CAN BE REPLACED WITH C-11 980-7

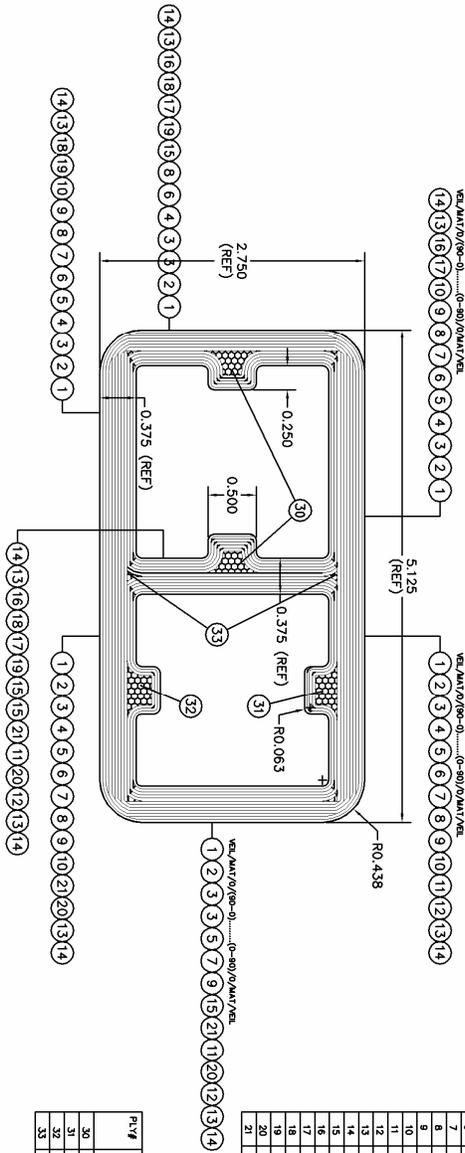

PROFILE #1 - VERTICAL MEMBER
(UPSTREAM VIEW)

- NOTES:
1. RESIN SPECIFIC GRAVITY = 1.12
 2. GLASS SPECIFIC GRAVITY = 2.62
 3. WEIGHT RATIO:
GLASS = 66.1 %
RESIN = 33.9 %
 4. GROSS SECTIONAL AREA = 6.44 SQ. IN.
 5. LAMINATE DENSITY = .065 (lb/in³)
 6. TOTAL WEIGHT = 5.0 lbs/FT

EFFECTIVE DN	REV	REVISIONS	BY	DATE

RESIN INFORMATION
 RESIN MANUFACTURER: DOW
 NAME: DERAKANE MODIFICAL 640-900 (UNIMESTER)


PLY SCHEDULE LEGEND

PLY#	MAT TASK	QTY	MAT TYPE	ORIENTATION	NET WIDTH (in)	SUITED MAT DOWN FACTOR
1	1	1	A	VEL	14.99	15.75
2	2	1	B	MAT	14.83	15.75
3	2	2	C	O/WOVEN	9.45	9.7
4	1	1	C	O/WOVEN	11.72	12.0
5	1	1	C	O/WOVEN	11.72	12.0
6	1	1	C	O/WOVEN	11.71	12.0
7	1	1	C	O/WOVEN	11.69	12.0
8	1	1	C	O/WOVEN	11.64	12.0
9	2	2	C	O/WOVEN	4.89	4.8
10	2	2	C	O/WOVEN	6.72	7.0
11	1	1	C	O/WOVEN	6.48	7.0
12	1	1	C	O/WOVEN	6.48	7.0
13	2	2	B	MAT	9.18	9.4
14	2	2	A	VEL	8.87	9.87
15	4	4	C	O/WOVEN	2.19	2.3
16	2	2	C	O/WOVEN	8.87	9.4
17	1	1	C	O/WOVEN	7.05	7.25
18	1	1	C	O/WOVEN	7.05	7.25
19	1	1	C	O/WOVEN	7.16	7.25
20	1	1	C	O/WOVEN	6.88	7.0
21	1	1	C	O/WOVEN	6.92	7.0

PLY#	QTY	MAT TYPE	AREA (sq/ft)	NUMBER OF ENDS	113 YIELD	250 YIELD	113 YIELD (SPRUE BULKED)
30	2	ROUNDING	.083	11			
31	1	ROUNDING	.082	14			
32	1	ROUNDING	.089	16			
33	2	ROUNDING	.005	1			

PRELIMINARY

DESIGNED BY	DATE	APPROVED	DATE	TITLE
				Composite Support & Solutions, Inc.
444 11th Street, San Mateo, California 94071 Tel: (650) 574-3182 Fax: (650) 574-3183				
PROJECT NUMBER	DATE	SCALE	SHEET # OF #	REV.
P5007-0016		SCALE: NTS	SHEET 1 OF 1	

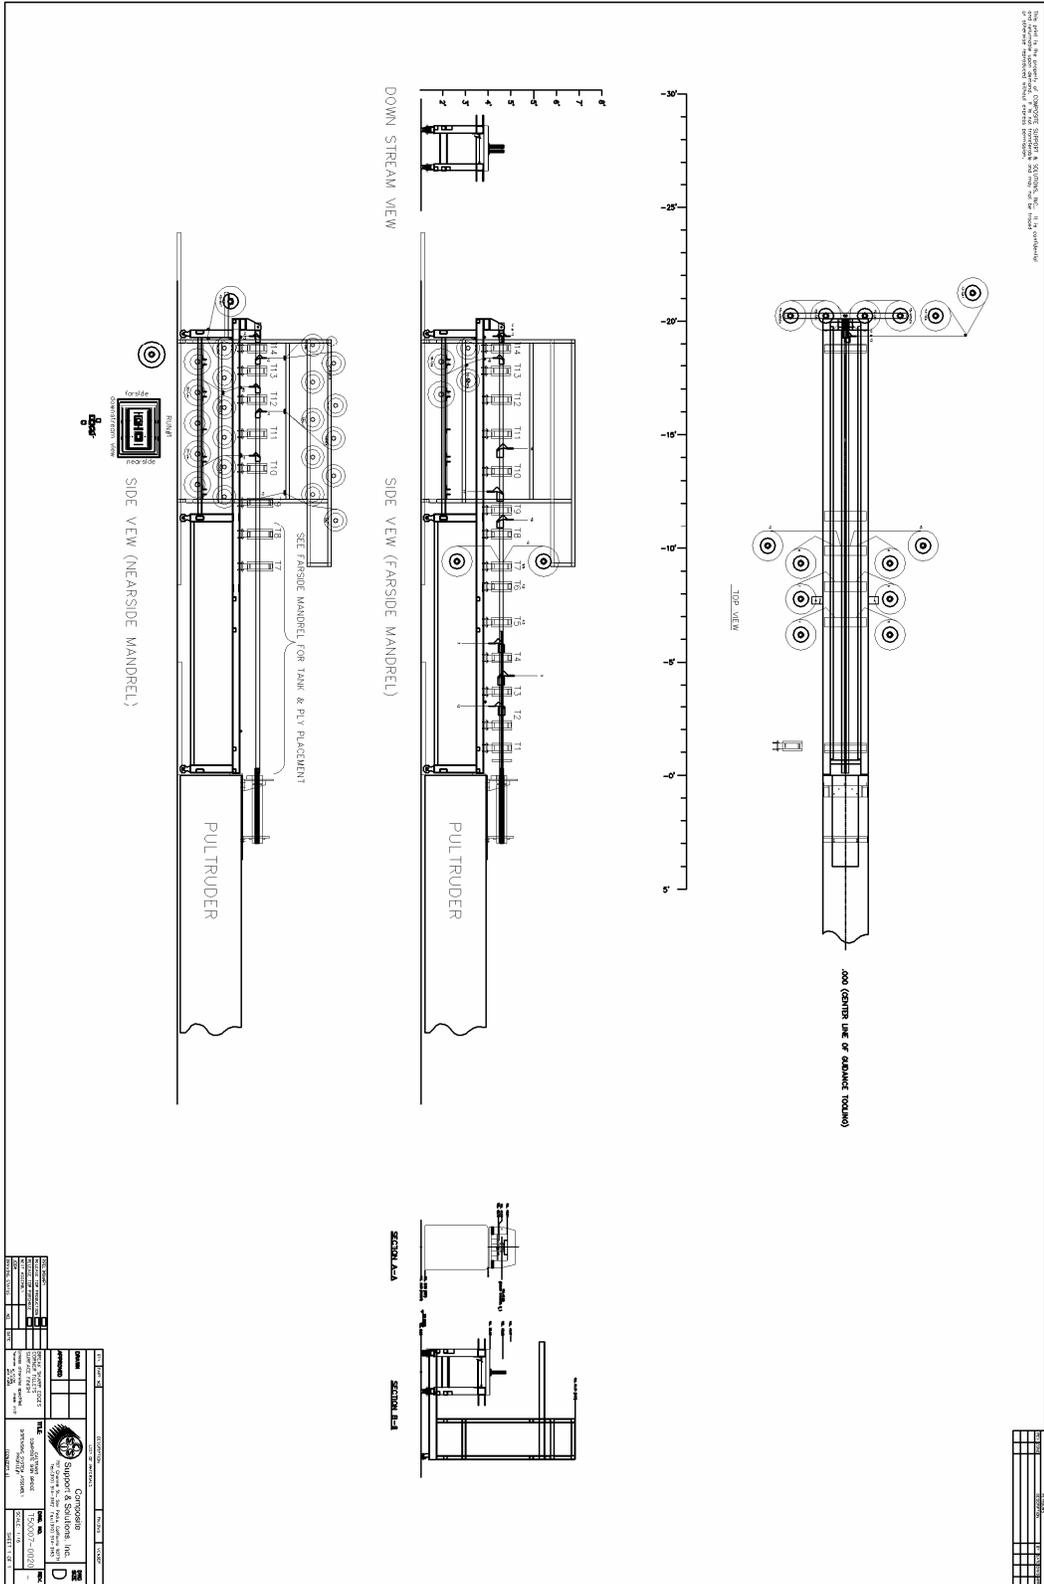

This part is the property of Composite Structures & Solutions, Inc. It is to be used only for the project and location specified. No part of this drawing is to be reproduced without the written permission of Composite Structures & Solutions, Inc.

DATE	DESCRIPTION

REV	DATE	DESCRIPTION

Composite Structures & Solutions, Inc.
 10000 Highway 100, Suite 100
 Houston, TX 77036
 Phone: 281-410-1000
 Fax: 281-410-1001
 Email: info@cssi.com

This print is the property of Composite Support & Solutions, Inc., it is confidential or otherwise reproduced without express permission.


*** COMPOSITE SUPPORT & SOLUTIONS INC. CONFIDENTIAL ***

MATERIAL LEGEND

MAT. TYPE	REINFORCEMENT COMPOSITION WEIGHT & ORIENTATION	WEIGHT (gr/ft ²) (oz/ft ²)	REGULATION (NUMBER / STYLE)
A	VEL. 100	.1	2014 RESINAY
B	MAT. CONTINUOUS	305	1 02/FT2 MAT
C	O/WOVEN(90)	50/29/25	1094
			311
			2014 RESINAY
			1 02/FT2 MAT
			1094
			311
			2014 RESINAY
			1 02/FT2 MAT
			1094
			311

NOTE: WR-725 CAN BE REPLACED WITH C-11 1808-7

NOTE:
 2014 RESINAY THICKNESS = 0.005"
 A130A THICKNESS = 0.014"
 WR725 THICKNESS = 0.018"
 E-LTW 1808-7 THICKNESS=0.019"

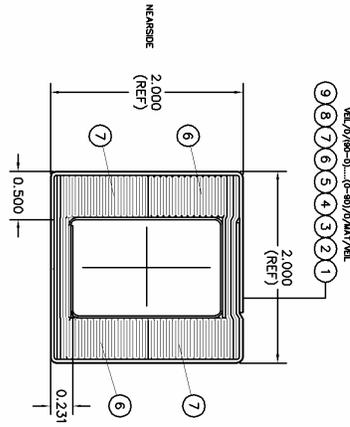

- NOTES:
1. RESIN SPECIFIC GRAVITY = 1.12
 2. GLASS SPECIFIC GRAVITY = 2.62
 3. WEIGHT RATIO:
 GLASS = 62.8 %
 RESIN = 37.2 %
 4. CROSS SECTIONAL AREA: = 2.5 SQ. IN.
 5. LAMINATE DENSITY = .062 (lb/in³)
 6. TOTAL WEIGHT = 1.86 lbs/FT

PROFILE #2 - HORIZONTAL/DIAGONAL MEMBER
 (UPSTREAM VIEW)

PRELIMINARY

EFFECTIVE DN	REV.	REVISIONS	BY	DATE

RESIN INFORMATION
 RESIN MANUFACTURER: DOW
 NAME: DERAKANE MODERUM 640-900 (VINYLESTER)

PLY SCHEDULE LEGEND

PLY#	MAT. TASK	QTY.	MAT. TYPE	ORIENTATION	NET WIDTH (in)	SUITED MAT. DOWN FACTOR
1	1	1	A	VEL.	8.83	8.0
2	1	1	C	MAT	8.83	8.0
3	2	2	C	O/WOVEN	2.0	2.0
4	2	2	C	O/WOVEN	2.0	2.0
5	2	2	C	O/WOVEN	2.0	2.0
6	2	2	C	O/WOVEN	12.91	13.0
7	2	2	C	O/WOVEN	13.79	14.0
8	1	1	B	MAT	6.15	6.25
9	1	1	A	VEL.	6.15	6.25


PLY#	QTY.	MAT. TYPE	AREA (in ²)	NUMBER OF ENDS	113 YIELD	250 YIELD	110 YIELD (DRUM)
20	?	?	?	?			

DESIGNED BY	DATE	APPROVED	TITLE
DRAWN BY	DATE	DATE	PROJECT NO.
SCALE	DATE	DATE	PROJECT NAME

Composite Support & Solutions, Inc.
 444 11th Street, San Mateo, California 94401
 Tel: (650) 514-3182 Fax: (650) 514-3183

PROJECT NO. P50007-0021
 SCALE: 1/2"=1'-0"
 SHEET 1 OF 1

This part is a component of Composite Support & Solutions, Inc. and is the intellectual property of Composite Support & Solutions, Inc. All rights reserved.

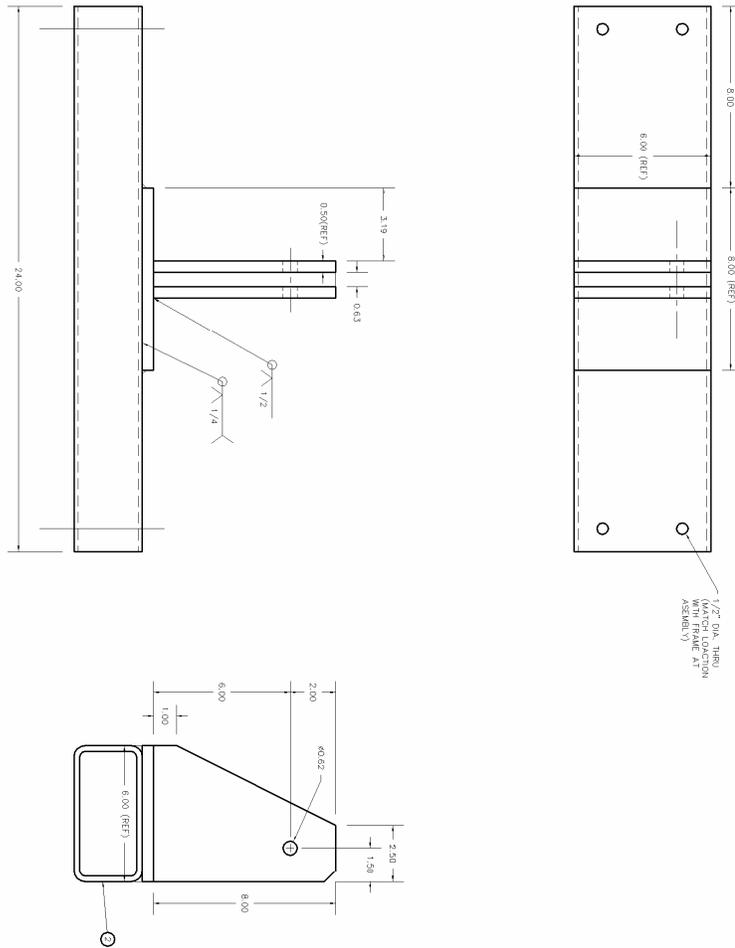


-1- ANCHOR BASE (PROFILE 2)

** PRELIMINARY **


Composite Support & Solutions, Inc. 10000 W. 10th Street Suite 100 Overland Park, KS 66204 Phone: 913.241.1100 Fax: 913.241.1101 Email: sales@cs-s.com	Project No.: P5007-0023 Drawing No.: 2023-11-15
--	--

Revision Description Date	1 Initial Release 11/15/23
---------------------------------	----------------------------------


This drawing is the property of Composite Structures, Inc. and is not to be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, mechanical, photocopying, recording, or by any information storage and retrieval system, without the prior written permission of Composite Structures, Inc.

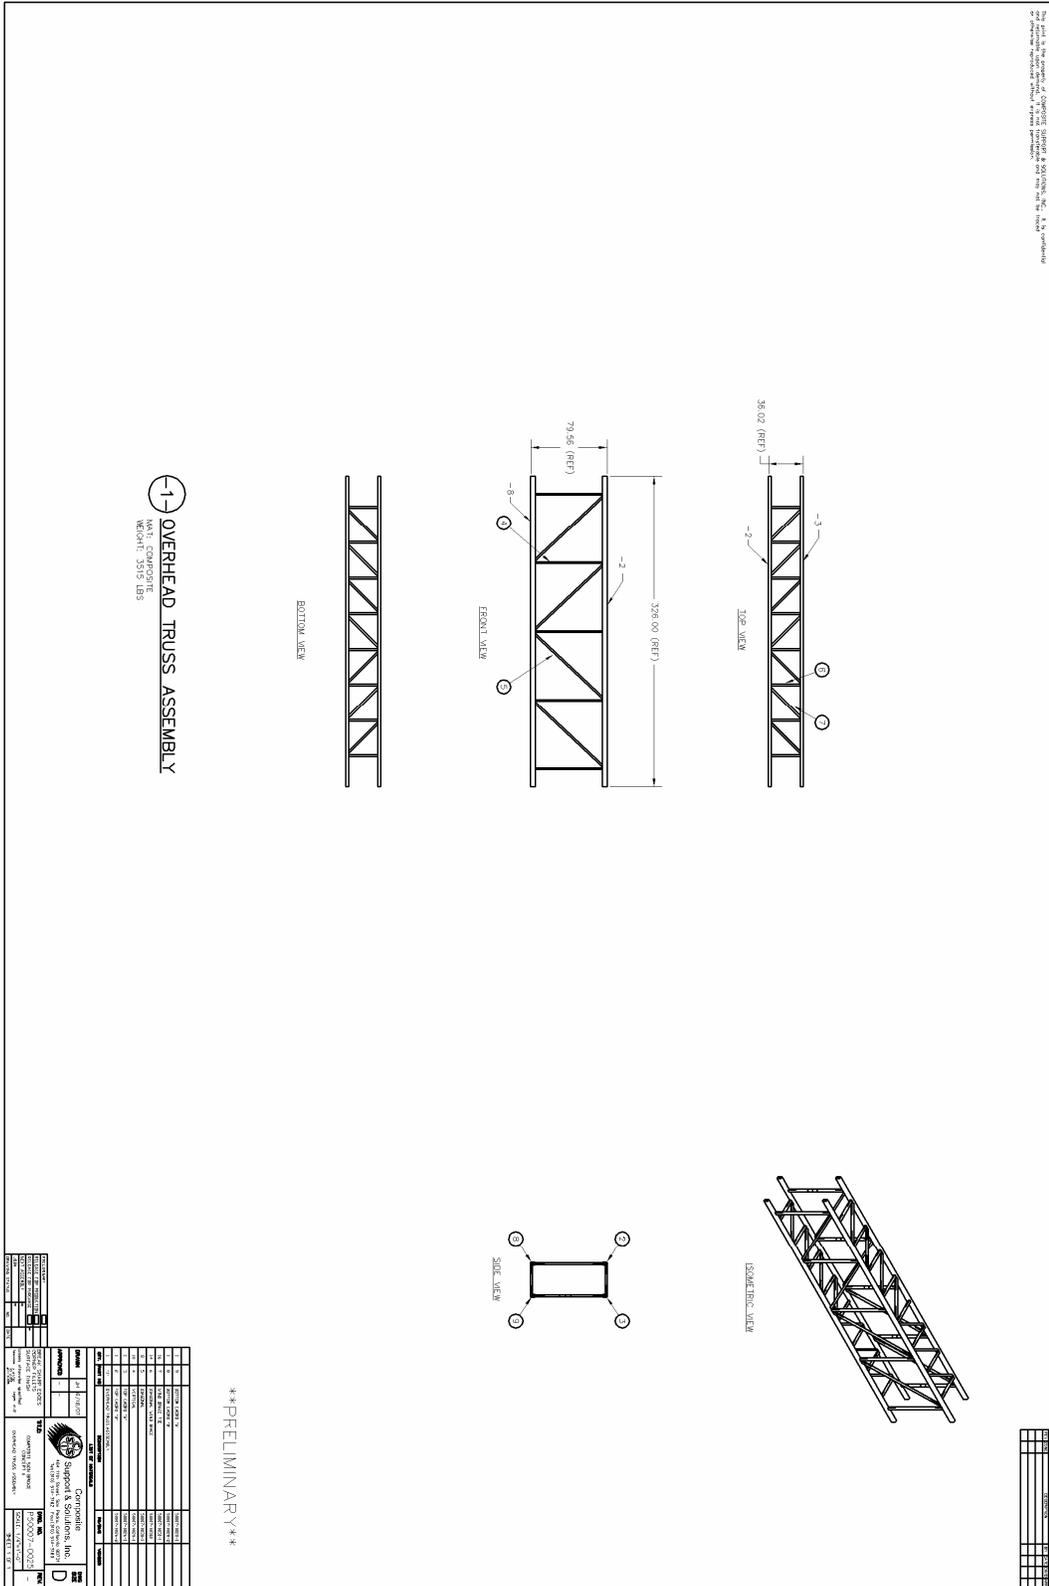

This drawing is the property of the Contractor. It shall remain the property of the Contractor and shall not be used for any other project without the written consent of the Contractor.

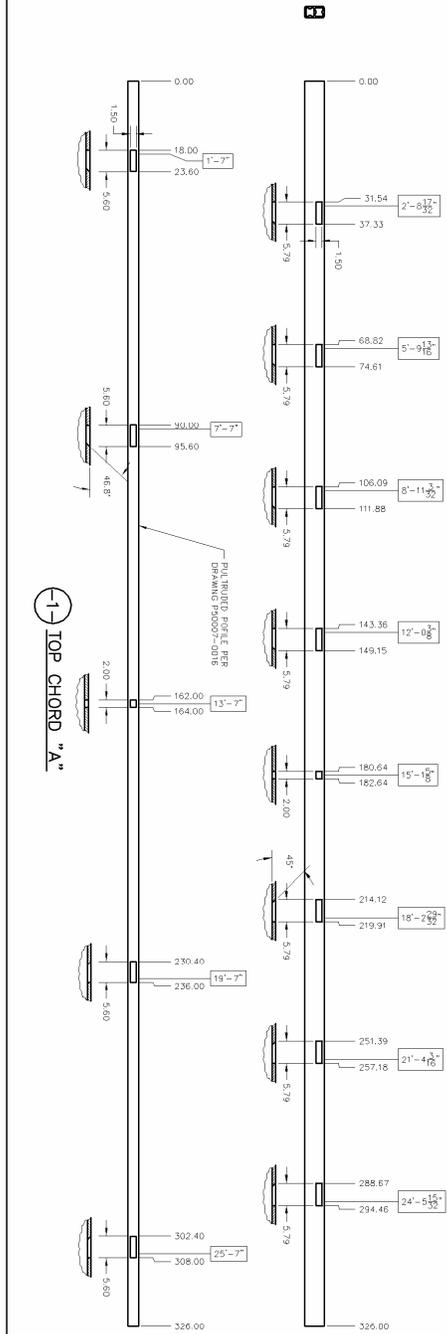


-1- TOP CHORD "A"

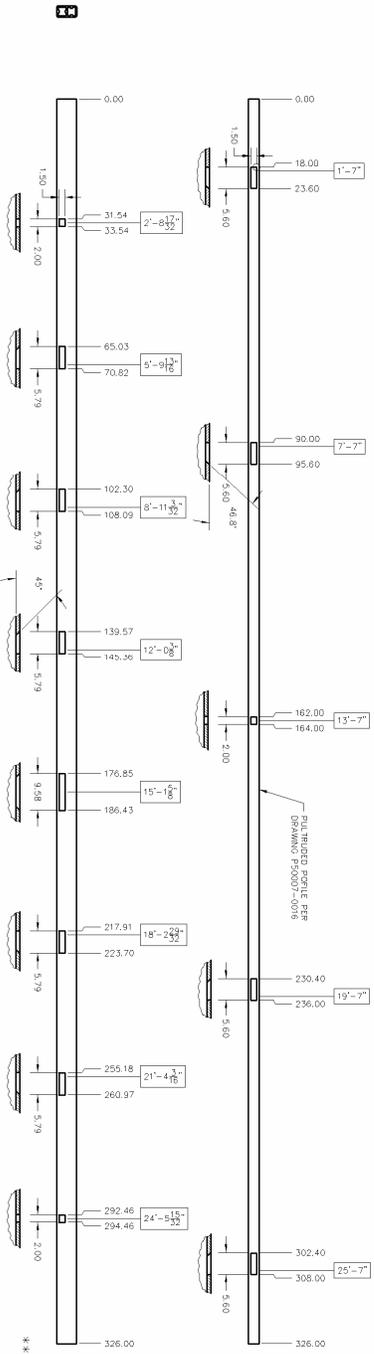


-2- TOP CHORD "B"

** PRELIMINARY **

PROJECT NO.	P5007-0026
DATE	11/11/11
SCALE	AS SHOWN
DRAWN BY	...
CHECKED BY	...
APPROVED BY	...
COMPANY	Compende Support & Solutions, Inc.
ADDRESS	11111 1st Street, Suite 100, San Diego, CA 92121
PHONE	(619) 444-1111
FAX	(619) 444-1112
WEBSITE	www.compende.com

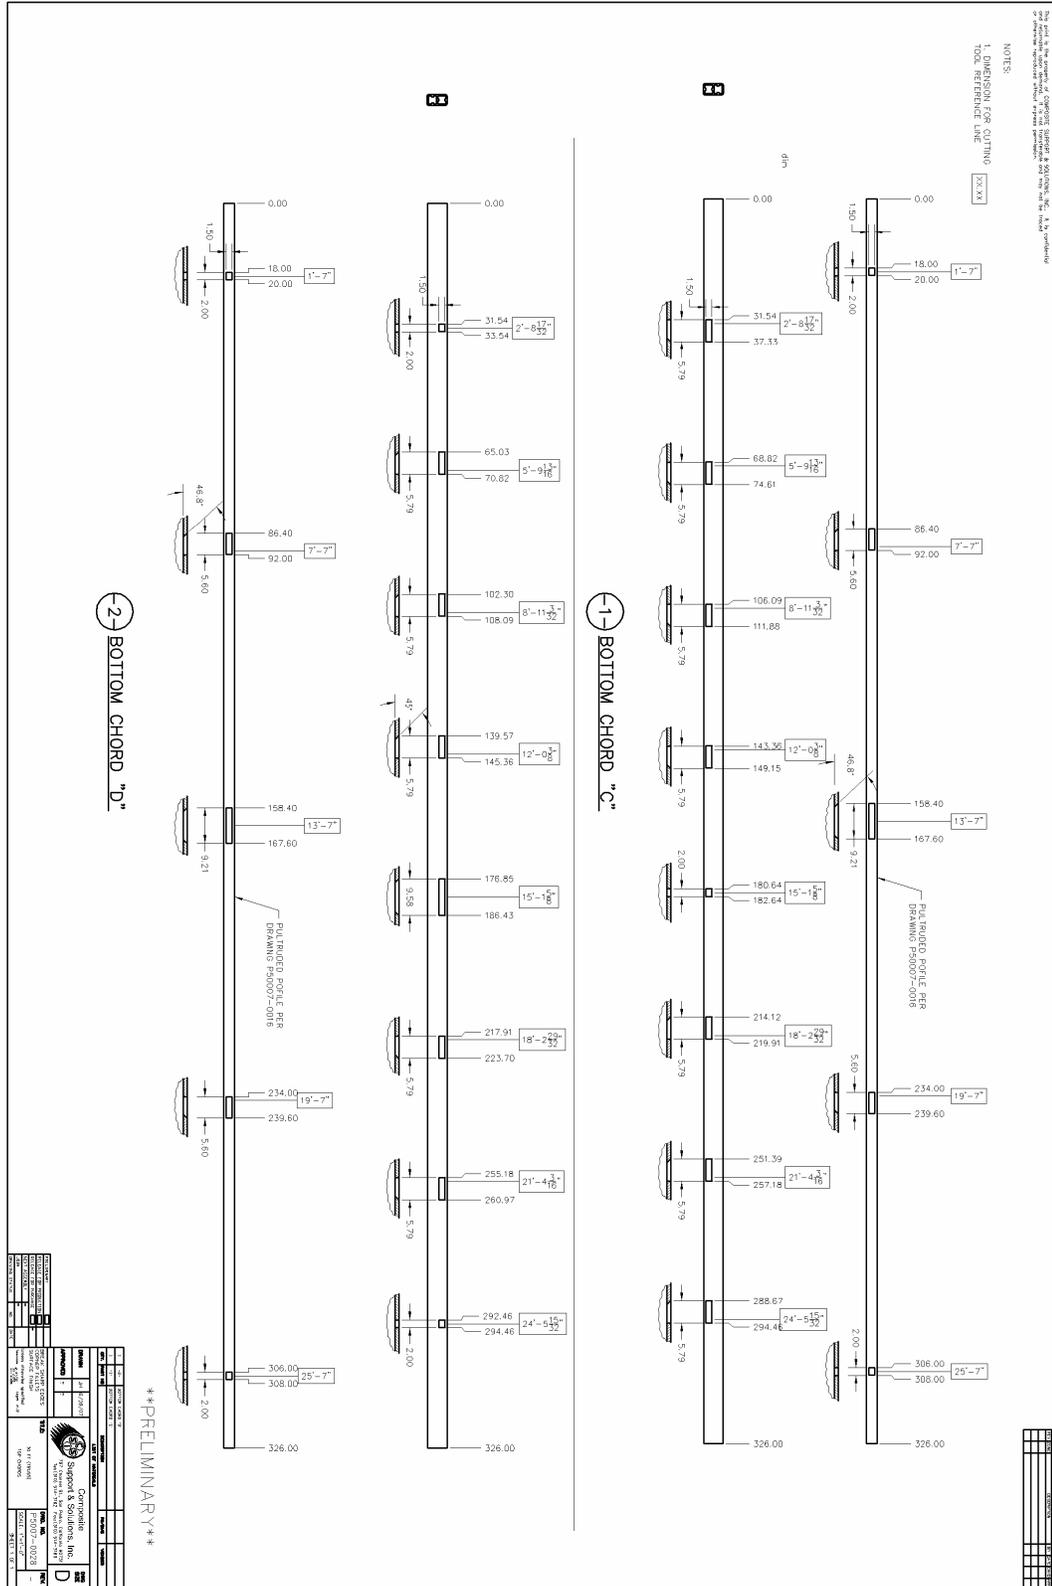

This drawing is the property of Composite Support & Solutions, Inc. It is to be used only for the project and location specified. It is not to be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, mechanical, photocopying, recording, or by any information storage and retrieval system, without the prior written permission of Composite Support & Solutions, Inc.

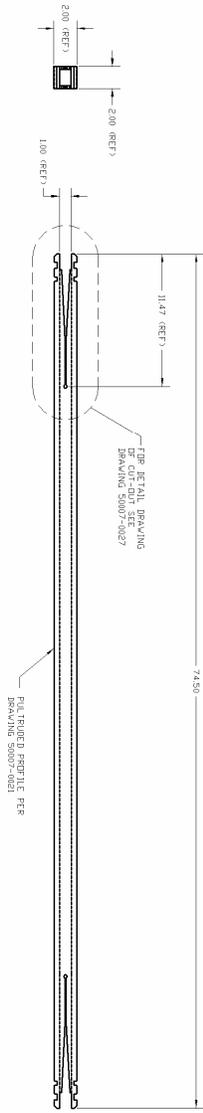


-1- VERTICAL

PRELIMINARY

Composite Support & Solutions, Inc. 14775 Highway 101, Suite 100 San Diego, CA 92126 (619) 444-1111 www.compositesupport.com		Project No. P5007-0029 Drawing No. CS-0029-01
Title: Vertical Pipe Section Date: 10/15/2019 Scale: 1/8" = 1'-0"	Author: J. Smith Designer: J. Smith Checker: J. Smith Engineer: J. Smith	Client: [Redacted] Location: [Redacted]

NO.	DATE	DESCRIPTION
1	10/15/2019	Issue for Construction

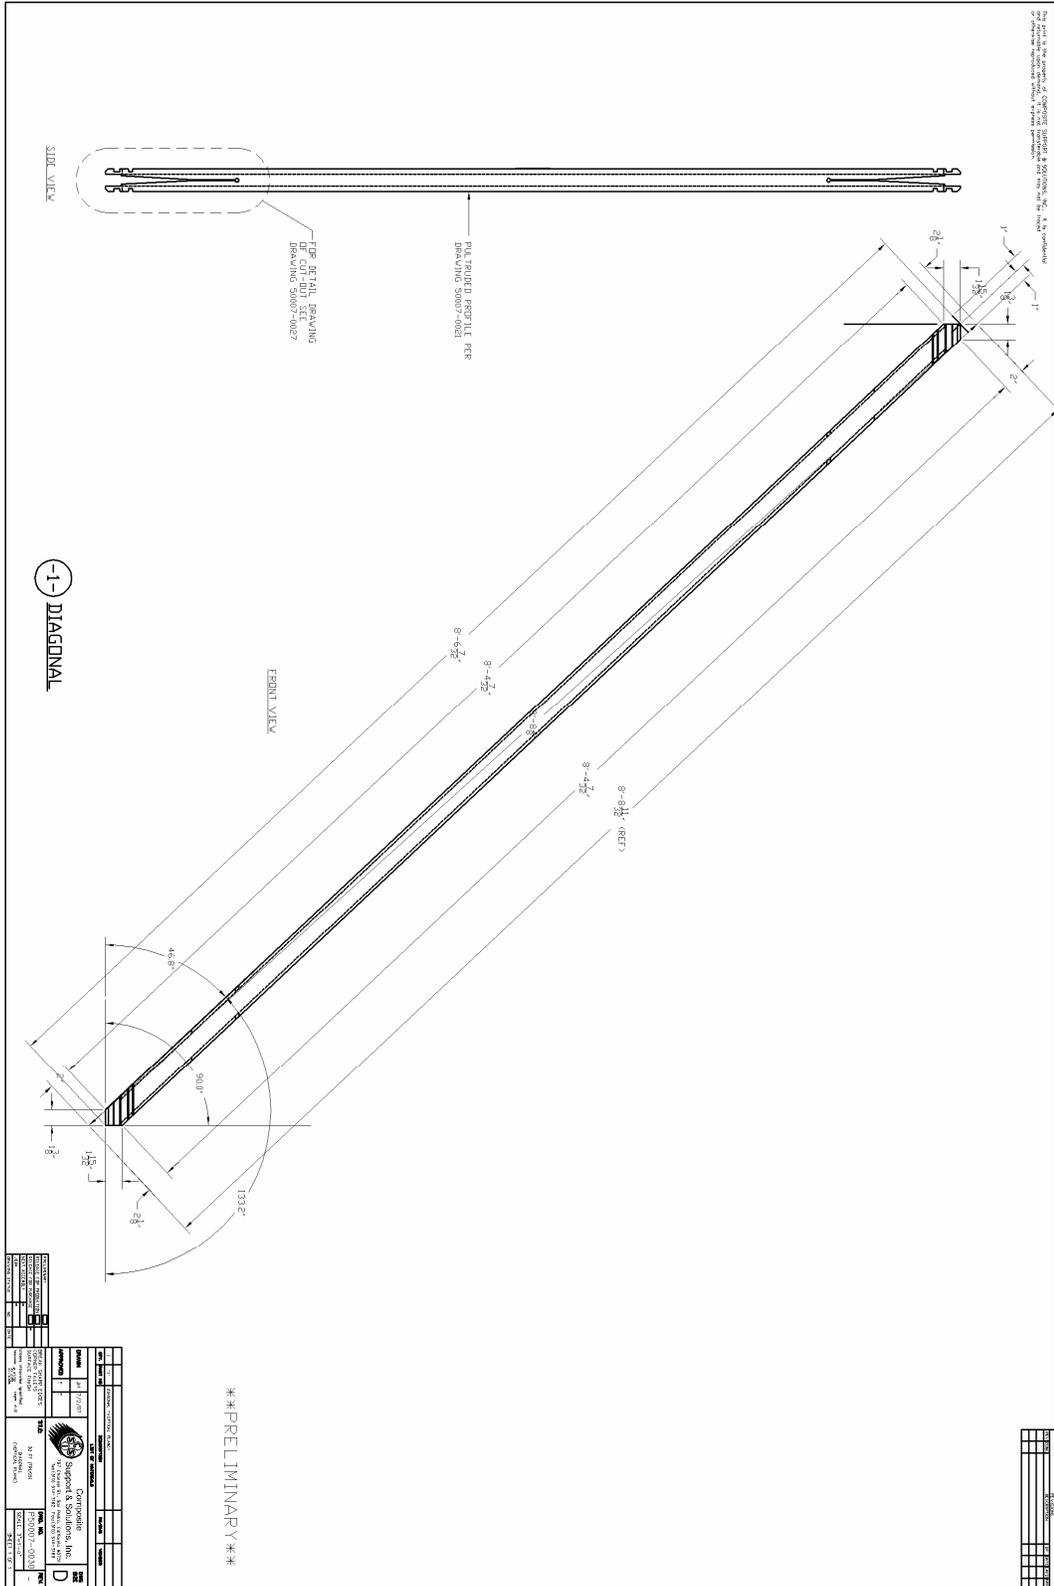

NO.	REV.	DATE	BY	CHKD.

NO.	REV.	DATE	BY	CHKD.



PROJECT	CONCRETE
NO.	50007-0030
DATE	11/11/11
BY	J. J. J.
CHKD.	J. J. J.
SCALE	AS SHOWN
APP'D.	J. J. J.
DATE	11/11/11

Comprehensive
 Support & Solutions, Inc.
 11111 11th Street
 Suite 100
 San Diego, CA 92121
 (619) 444-1111
 www.compsupport.com

Be part of the world of Composite Structures & Solutions, Inc. All dimensions are in feet unless otherwise specified. All dimensions are in feet unless otherwise specified.

54' SPAN BRIDGE ASSEMBLY


NOTES
1. ALL DIMENSIONS ARE IN INCHES

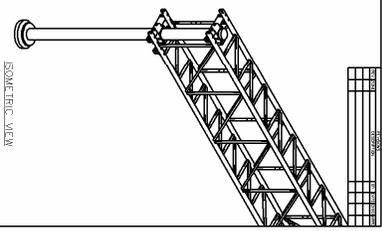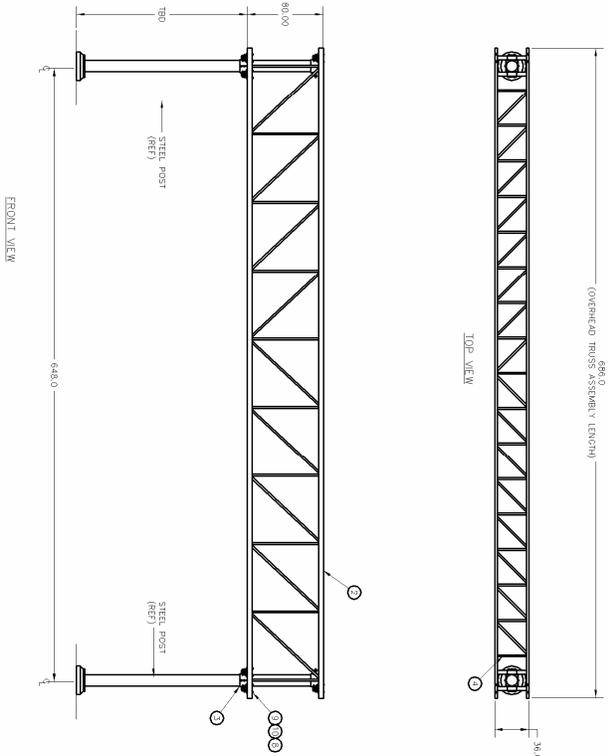


PRELIMINARY

NO.	DESCRIPTION	QTY	UNIT	REMARKS
1	STEEL POST	2	EA	
2	STEEL POST	2	EA	
3	STEEL POST	2	EA	
4	STEEL POST	2	EA	
5	STEEL POST	2	EA	
6	STEEL POST	2	EA	
7	STEEL POST	2	EA	
8	STEEL POST	2	EA	
9	STEEL POST	2	EA	
10	STEEL POST	2	EA	
11	STEEL POST	2	EA	
12	STEEL POST	2	EA	
13	STEEL POST	2	EA	
14	STEEL POST	2	EA	
15	STEEL POST	2	EA	
16	STEEL POST	2	EA	
17	STEEL POST	2	EA	
18	STEEL POST	2	EA	
19	STEEL POST	2	EA	
20	STEEL POST	2	EA	
21	STEEL POST	2	EA	
22	STEEL POST	2	EA	
23	STEEL POST	2	EA	
24	STEEL POST	2	EA	
25	STEEL POST	2	EA	
26	STEEL POST	2	EA	
27	STEEL POST	2	EA	
28	STEEL POST	2	EA	
29	STEEL POST	2	EA	
30	STEEL POST	2	EA	
31	STEEL POST	2	EA	
32	STEEL POST	2	EA	
33	STEEL POST	2	EA	
34	STEEL POST	2	EA	
35	STEEL POST	2	EA	
36	STEEL POST	2	EA	
37	STEEL POST	2	EA	
38	STEEL POST	2	EA	
39	STEEL POST	2	EA	
40	STEEL POST	2	EA	
41	STEEL POST	2	EA	
42	STEEL POST	2	EA	
43	STEEL POST	2	EA	
44	STEEL POST	2	EA	
45	STEEL POST	2	EA	
46	STEEL POST	2	EA	
47	STEEL POST	2	EA	
48	STEEL POST	2	EA	
49	STEEL POST	2	EA	
50	STEEL POST	2	EA	

For use in the design of overhead truss structures, this drawing is preliminary and subject to change without notice. It is the user's responsibility to verify the accuracy of the information provided.

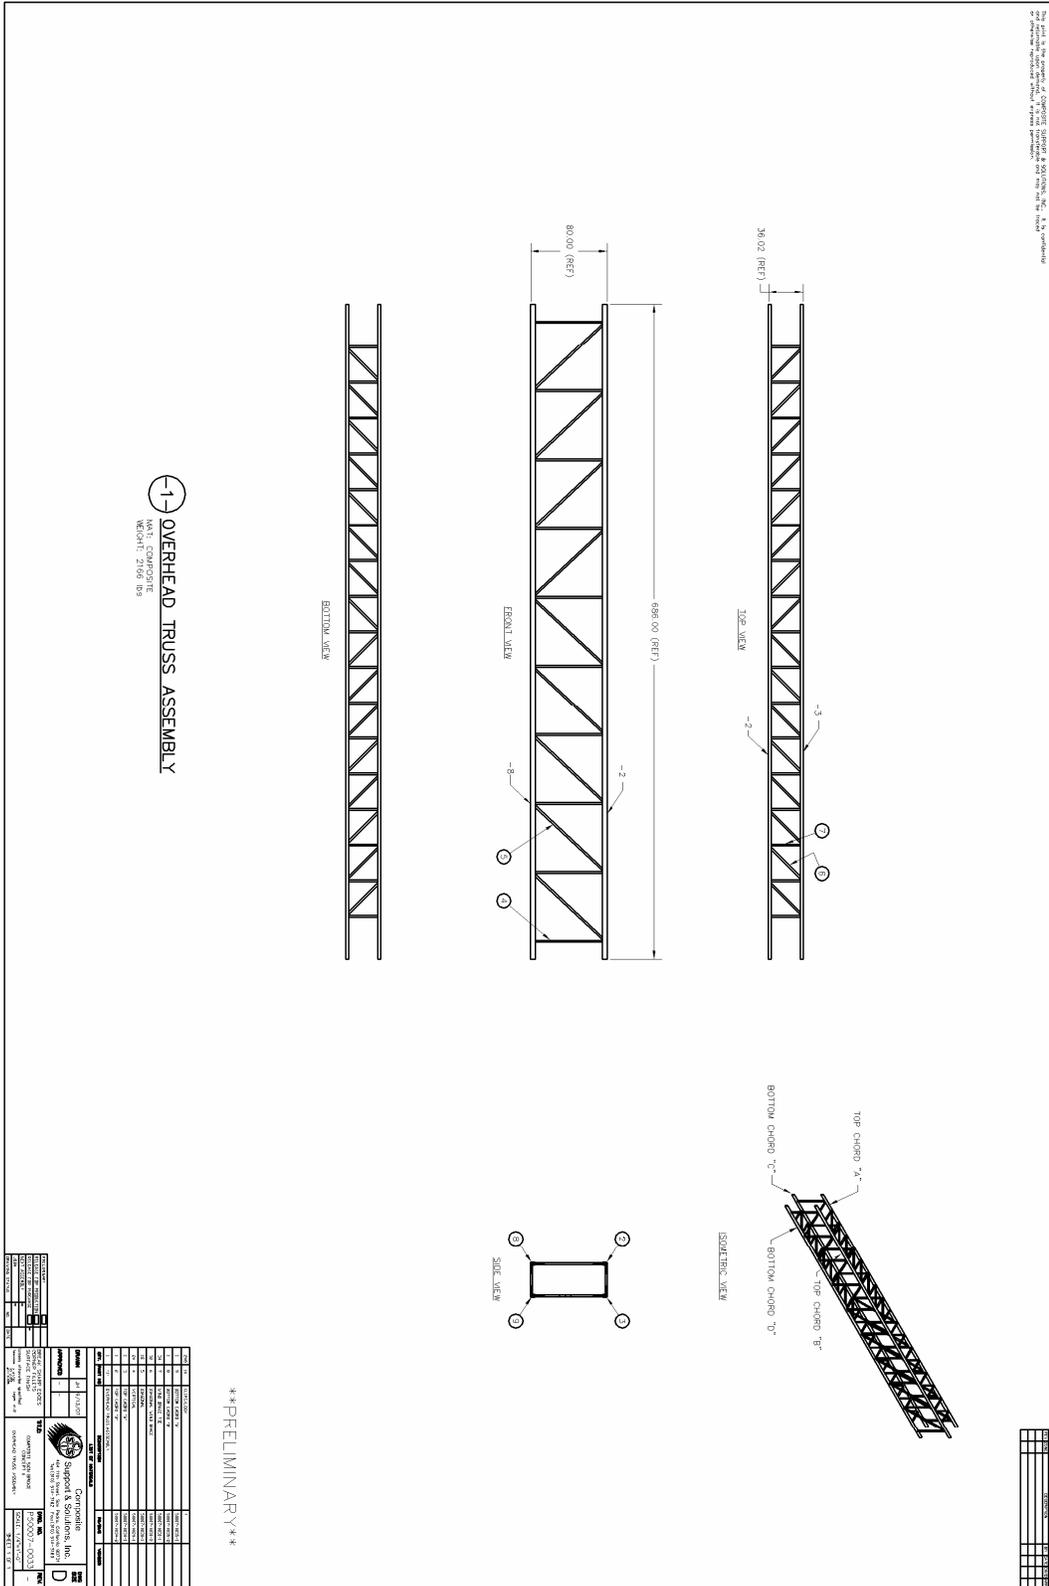

Part of a registered or copyright interest in the work of the inventor or other person to whom the right of invention has been assigned.

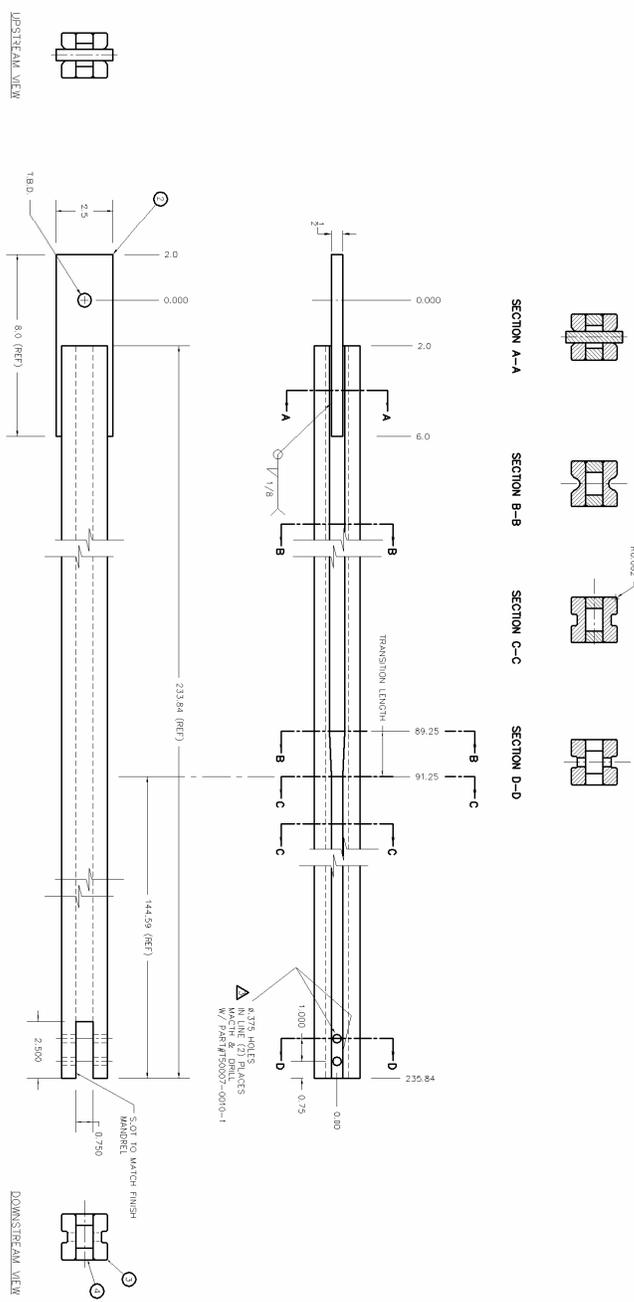


NOTE:
 1. PARTS SHALL BE STRESS RELIEF AFTER WELDING.
 2. DIMENSIONS SHOWN ARE FINAL INSPECTED DIMENSIONS AFTER MACHINING, PAINTING & PLATING.
 3. MATCH & DRILL WITH PART # 150007-0010-1

1-1 ROUGH MANDREL "TYPE C" - FAR SIDE
 MATERIAL: ALUMINUM


REV	DATE	DESCRIPTION	BY	CHKD
1	08/11/2011	ISSUED FOR MANUFACTURE	WJ	WJ
2	08/11/2011	REVISION	WJ	WJ
3	08/11/2011	REVISION	WJ	WJ
4	08/11/2011	REVISION	WJ	WJ
5	08/11/2011	REVISION	WJ	WJ
6	08/11/2011	REVISION	WJ	WJ
7	08/11/2011	REVISION	WJ	WJ
8	08/11/2011	REVISION	WJ	WJ
9	08/11/2011	REVISION	WJ	WJ
10	08/11/2011	REVISION	WJ	WJ
11	08/11/2011	REVISION	WJ	WJ
12	08/11/2011	REVISION	WJ	WJ
13	08/11/2011	REVISION	WJ	WJ
14	08/11/2011	REVISION	WJ	WJ
15	08/11/2011	REVISION	WJ	WJ
16	08/11/2011	REVISION	WJ	WJ
17	08/11/2011	REVISION	WJ	WJ
18	08/11/2011	REVISION	WJ	WJ
19	08/11/2011	REVISION	WJ	WJ
20	08/11/2011	REVISION	WJ	WJ
21	08/11/2011	REVISION	WJ	WJ
22	08/11/2011	REVISION	WJ	WJ
23	08/11/2011	REVISION	WJ	WJ
24	08/11/2011	REVISION	WJ	WJ
25	08/11/2011	REVISION	WJ	WJ
26	08/11/2011	REVISION	WJ	WJ
27	08/11/2011	REVISION	WJ	WJ
28	08/11/2011	REVISION	WJ	WJ
29	08/11/2011	REVISION	WJ	WJ
30	08/11/2011	REVISION	WJ	WJ
31	08/11/2011	REVISION	WJ	WJ
32	08/11/2011	REVISION	WJ	WJ
33	08/11/2011	REVISION	WJ	WJ
34	08/11/2011	REVISION	WJ	WJ
35	08/11/2011	REVISION	WJ	WJ
36	08/11/2011	REVISION	WJ	WJ
37	08/11/2011	REVISION	WJ	WJ
38	08/11/2011	REVISION	WJ	WJ
39	08/11/2011	REVISION	WJ	WJ
40	08/11/2011	REVISION	WJ	WJ
41	08/11/2011	REVISION	WJ	WJ
42	08/11/2011	REVISION	WJ	WJ
43	08/11/2011	REVISION	WJ	WJ
44	08/11/2011	REVISION	WJ	WJ
45	08/11/2011	REVISION	WJ	WJ
46	08/11/2011	REVISION	WJ	WJ
47	08/11/2011	REVISION	WJ	WJ
48	08/11/2011	REVISION	WJ	WJ
49	08/11/2011	REVISION	WJ	WJ
50	08/11/2011	REVISION	WJ	WJ

This part is a component of Composite Support & Solutions, Inc. All dimensions are in inches unless otherwise specified. All dimensions are to be maintained unless otherwise specified.

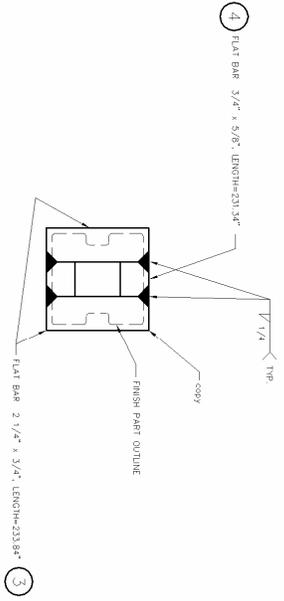


WELDMENT DRAWING

SECTION B-B
(MACHINING DRAWING)



SECTION C-C
(MACHINING DRAWING)

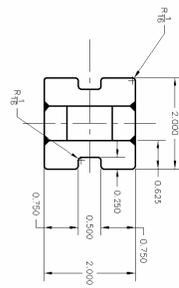

PRELIMINARY

DATE	BY	DESCRIPTION
01/15/2025	AS	ISSUE FOR MANUFACTURE
01/15/2025	AS	ISSUE FOR MANUFACTURE
01/15/2025	AS	ISSUE FOR MANUFACTURE
01/15/2025	AS	ISSUE FOR MANUFACTURE
01/15/2025	AS	ISSUE FOR MANUFACTURE

COMPONENT	COMPOSITE SUPPORT & SOLUTIONS, INC.
DESCRIPTION	COMPOSITE SUPPORT & SOLUTIONS, INC.
DATE	01/15/2025
BY	AS
APPROVED	AS
DATE	01/15/2025


This print is the property of Composite Support & Solutions, Inc., it is confidential and may not be used or otherwise reproduced without express permission.

*** COMPOSITE SUPPORT & SOLUTIONS INC. CONFIDENTIAL ***

MATERIAL LEGEND

MAT TYPE	REINFORCEMENT	COMPRESSION WEIGHT & ORIENTATION	WEIGHT (gr/ft ²) (oz/ft ²)	REGULATION (NUMBER / STYLE)
A	VEL	100	.1	2014 RESINAY
B	MAT	CONTINUOUS	305	1 02/FT2 MAT
C	0	100%	130	A150

update w/ notes

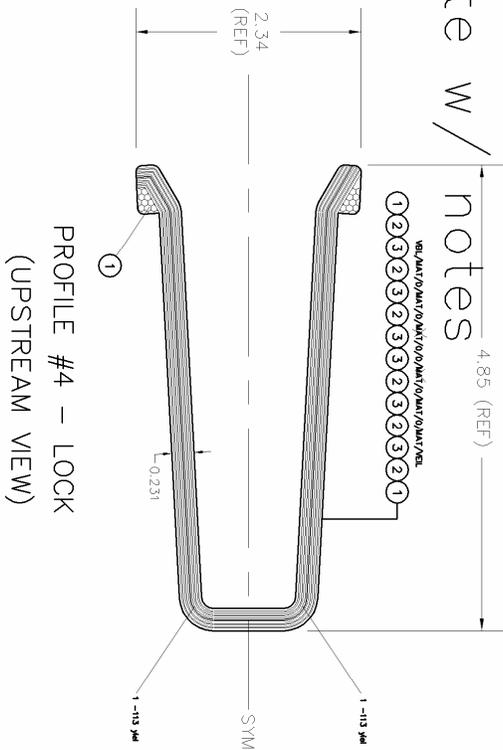

PROFILE #4 - LOCK
(UPSTREAM VIEW)

NOTES:

EFFECTIVE DN	REV	REVISIONS	BY	DATE
	A	CHANGED LAY-UP	JL	7/19/07

RESIN INFORMATION
 RESIN MANUFACTURER: DOW
 NAME: DERAKANE MODERUM 640-900 (UNVESTER)

PLY SCHEDULE LEGEND

PLY#	MAT	QTY	MAT TYPE	ORIENTATION	NET WIDTH (in)	SPLIT MAT
1	1	1	A	VEL	12.0	7
2	1	1	B	MAT	10.8	7
3	2	2	C	0	10.8	7

PLY#	QTY	MAT TYPE	AREA (in ²)	NUMBER OF ENDS	113 YIELD	250 YIELD	113 YIELD (EPRI) (BULKED)
20	2	ROUND	0.40	9			

PRELIMINARY

DESIGNED BY	DATE	APPROVED	DATE
DESIGNED BY	DATE	APPROVED	DATE

Composite Support & Solutions, Inc.
 441 11th Street, San Mateo, California 90751
 Tel: (310) 514-3182 Fax: (310) 514-3183

TITLE: STRUCTURAL MEMBERS FOR MAT P50009-1004
 SCALE: NTS
 SHEET 1 OF 1

